

## Prediction of atmospheric corrosion from meteorological parameters: Case of the atmospheric basin of the Costa Rican Western Central Valley

Javier E. RODRÍGUEZ-YÁÑEZ<sup>1\*</sup>, Erick RIVERA-FERNÁNDEZ<sup>2</sup>, Daniel ALVARADO-GONZÁLEZ<sup>3</sup>,  
Mariela ABDALAH-HERNÁNDEZ<sup>3</sup> and Rafael QUIRÓS-QUIRÓS<sup>4</sup>

<sup>1</sup>*Urban Ecology Research Laboratory, Costa Rica Distance University, 474-2050, Mercedes de Montes de Oca, San José, Costa Rica.*

<sup>2</sup>*School of Physics and Center for Geophysical Research, University of Costa Rica, 11501-2060, San Pedro de Montes de Oca, San José, Costa Rica.*

<sup>3</sup>*Advanced Computing Laboratory, National High Technology Center, 1174-1200, Pavas, San José, Costa Rica.*

<sup>4</sup>*School of Geography, University of Costa Rica, 11501-2060, San Pedro de Montes de Oca, San José, Costa Rica.*

\*Corresponding author; email: jrodriguezy@uned.ac.cr

Received: August 26, 2020; accepted: April 20, 2021

### RESUMEN

La evaluación de la corrosión atmosférica se basa actualmente en el estudio de las cuencas atmosféricas (AB, por sus siglas en inglés). La modelización de la corrosión atmosférica implica en muchos casos la medición de varios parámetros meteorológicos y de contaminación atmosférica, concretamente la temperatura, la humedad relativa, el cloruro y el dióxido de azufre, lo que hace más complejo el proceso de estimación. Sin embargo, para el Valle Central Occidental (WCV, por sus siglas en inglés) de Costa Rica, un AB de baja contaminación, es posible desarrollar modelos simplificados de corrosión atmosférica, basados en un pequeño número de parámetros atmosféricos. En este trabajo se analizaron las variables meteorológicas de la región de estudio en cuanto a su dependencia de la altitud y su aplicabilidad en el desarrollo de un modelo simplificado para predecir la tasa de corrosión (Vcorr). El resultado del modelo de predicción se comparó con el modelo estándar de la norma ISO 9223:2012, mostrando una mayor habilidad y dando resultados fiables para un amplio intervalo de altitudes.

### ABSTRACT

The assessment of atmospheric corrosion is currently based on the study of atmospheric basins (AB). Modeling atmospheric corrosion in many cases involves the measurement of several meteorological and atmospheric pollution parameters, specifically temperature, relative humidity, chloride, and sulfur dioxide, making the estimation process more complex. However, for the Western Central Valley (WCV) in Costa Rica, a low-pollution AB, it is possible to develop simplified atmospheric corrosion models based on a small number of atmospheric parameters. In this paper, the meteorological variables of the study region were analyzed in terms of their dependency on altitude and their applicability in the development of a simplified model to predict the corrosion rate (Vcorr). The output of the predictive model was compared with the standard model of ISO 9223:2012, showing a higher skill and giving reliable results for a wide interval of altitudes.

**Keywords:** atmospheric basin, corrosion, meteorological parameters, basic modeling.

## 1. Introduction

The Costa Rican Western Central Valley (WCV) is limited to the northwest by the Central Volcanic mountain range, to the east by the hills of Ochomogo, and to the southwest by the foothills of the Talamanca mountain range. The average altitude of the WCV is about 1000 m above sea level (m.a.s.l.), with values up to 2000 m.a.s.l. in some places (IMN, 2008).

The region's average annual precipitation is 2300 mm, with two clearly marked seasons: a rainy season from May to November and a dry season from December to April. During the rainy season, a relative minimum of precipitation occurs in July-August, known as the *veranillo* or mid-summer drought (Magaña et al., 1999). Temperature and relative humidity show small changes, with average values of 20 °C and 75 %, respectively, varying with altitude and the time of the year (Solano and Villalobos, 2000; IMN, 2008). The predominant winds are the trade winds that blow from the northeast to the southwest. The Central Volcanic mountain range allows the passage of trade winds over the mountains or through mountain passes (mainly the gaps of La Palma and Desengaño). The seasonal variation of wind intensity, associated with the Caribbean low-level jet, determines most of the climatic changes in the WCV (Muñoz et al., 2002; Amador, 2008). Another characteristic pattern of the wind in the WCV is related to mountain-valley circulations. These are generated by temperature differences between both geographic landforms during the day, causing the wind to move from the mountain to the valley in the morning and in the opposite direction in the afternoon (Zárate, 1978; Barrantes et al., 1985). Due to the climatic and orographic conditions of the WCV, this area can be considered an Atmospheric Basin (AB). Here the climatic variability, circulation, and dispersion of air pollutants are driven mainly by the prevailing direction of winds and orography (Zárate, 1980; Muñoz et al., 2002; Caetano and Iniesta, 2008; García-Reynoso et al., 2009; Herrera et al., 2012; SEMARNAT-INECC, 2016).

Metallic materials are thermodynamically unstable under atmospheric conditions, which causes their deterioration, giving rise to the atmospheric corrosion phenomenon. A usual way to evaluate this process is by obtaining the loss of material in a fundamental state with respect to the time of exposure to the

environment. This way allows the corrosion rate estimation as a loss of mass per unit area ( $\text{mg m}^{-2} \text{y}^{-1}$ ) or as a loss of sheet thickness ( $\mu\text{m y}^{-1}$ ) during the exposure time. Low carbon steel is the most common material for visualizing corrosion, similar to ASTM A36/A36M-19 (ASTM International, 2019).

Previous research by Morcillo et al. (2011) and the guidelines of the ISO 9223:2012 standard state that temperature (T), relative humidity (RH), chlorides ( $\text{Cl}^-$ ), and sulfur oxides ( $\text{SO}_2$ ) are the primary agents that contribute to corrosion. Temperature and relative humidity provide enough conditions for the material oxidation process, while pollutants modify the oxides formed on steel surfaces, producing distortion in the crystalline network and structural weakness. Consequently, materials turn more labile and porous, becoming more susceptible to corrosive attacks (Feliu et al., 1993; Morcillo et al., 2013; Díaz et al., 2018).

Temperature and relative humidity variables are obtained from meteorological data, and the deposition of both chlorides and sulfur oxides is measured or estimated by air pollution evaluation methods. These parameters permit the characterization of the effects of pollution variation on the corrosion rate in the WCV (Morcillo et al., 1998; Roberge et al., 2002; Morcillo et al., 2012; Robles, 2013; Garita-Arce et al., 2014; Rodríguez-Yáñez et al., 2015; Alcántara et al., 2015; Morcillo, 2017).

Garita-Arce et al. (2014) proposed a series of models for obtaining corrosion rates depending on the available information. For Costa Rica, maps of applicability of the corrosion models are based on the work of Rodríguez-Yáñez et al. (2015). These maps present an increasing complexity, starting from the Brooks deterioration index to the ISO 9223 (ISO, 1992) standard and using linear equations to model corrosion rate. The updated ISO 9223:2012 (ISO, 2012a) standard includes a new model for estimating corrosion. It considers the annual corrosion as a function of climatic and pollution variables.

## 2. Data and methods

Hourly meteorological data for several stations within the WCV were provided by the National Meteorological Institute and the Costa Rican Electricity Institute (IMN and ICE, respectively, by their Spanish acronyms). Figure 1 shows the location of the area

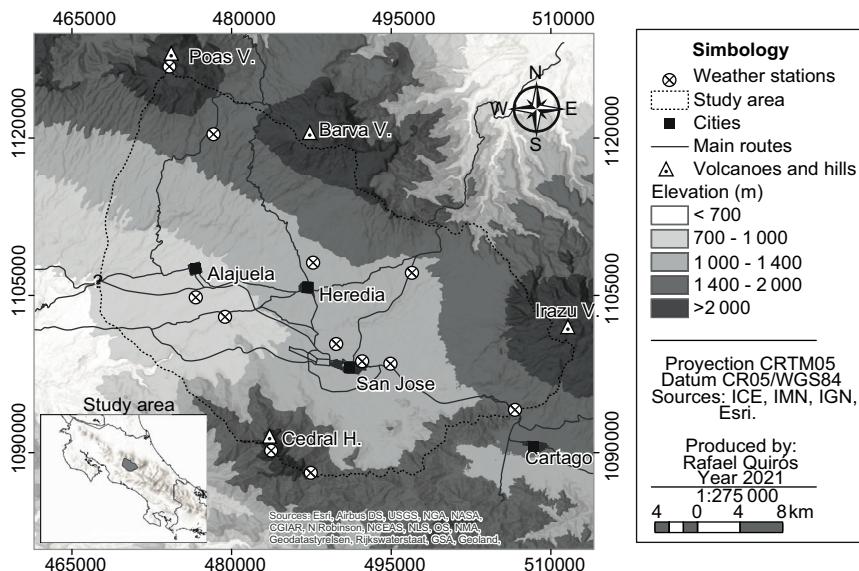


Fig. 1. Location of the WCV and the weather stations used for data collection.

of study. The analysis period was from 2010 to 2019 (see Table I). Only meteorological stations with less than 5 % of missing data were considered. From these data, the variables of interest were T and RH. The time of wetness (TOW), defined as the fraction of hours per year where T is greater than 0 °C and RH is greater than or equal to 80 %, was also obtained.

### 2.1 Atmospheric conditions and air pollution

Within the studied period, the number of both warm (El Niño) and cold (La Niña) phases of the El Niño-Southern Oscillation (ENSO) is similar (NOAA, 2019). ENSO episodes are linked to inter-annual variations in circulation and precipitation patterns over Costa Rica (Fernández et al. 2013).

On the other hand, the volcanic activity was low and spaced in time. It was mainly associated with eruptions of the Poás and Turrialba volcanoes in 2015. During most of these eruptive events, winds were not blowing toward the WCV (OVSICORI, 2015). Under these conditions, several authors have shown that pollution levels of chlorides and sulfur oxides in the WCV are about  $5 \text{ mg m}^{-2} \text{ d}^{-1}$  and  $10 \text{ mg m}^{-2} \text{ d}^{-1}$ , respectively (Robles, 2013; Herrera-Murillo et al., 2014). These levels correspond to a low polluted atmosphere.

### 2.2 Corrosion models

According to the results of Garita-Arce et al. (2014) for the low carbon steel, an estimation curve of the corrosion rate at the WCV can be derived from meteorological parameters, specifically RH and TOW. Corrosion rate ( $V_{\text{corr}}$ ) for the WCV is a linear function of TOW or RH, as given by the following equations:

$$V_{\text{corr}} = 0.949RH - 56.65 \quad R^2 = 0.930, \quad (1)$$

$$V_{\text{corr}} = 22.87TOW + 7.85 \quad R^2 = 0.953, \quad (2)$$

where,

$V_{\text{corr}}$ : corrosion rate,  $\mu\text{m y}^{-1}$ ,

TOW: fraction average annual hours of wetness, dimensionless,

RH: average annual relative humidity, %.

The above equations were determined for an altitude of 1108 m.a.s.l. in the La Sabana sector of San José, Costa Rica.

The ISO 9223:2012 standard contains guidelines to determine  $V_{\text{corr}}$ . One of them is to utilize the corrosion categories listed in Table II. A second alternative is to obtain it by employing model equations.

Table I. Location of the meteorological stations available in the WCV.

Name	North latitude	West longitude	Altitude (m.a.s.l)	Start date	End date
RECOPE, Ochomogo	09° 53' 40.2"	83° 56' 19.4"	1546	01/01/2010	31/01/2018
CIGEFI	09° 56' 11.0"	84° 02' 43.0"	1210	01/01/2010	31/01/2018
IMN, Aranjuez	09° 56' 16.6"	84° 04' 10.8"	1181	01/01/2010	31/01/2018
Juan Santamaría International airport	09° 59' 26.5"	84° 12' 52.9"	913	01/01/2010	15/02/2018
Fraijanes lake	10° 08' 14.4"	84° 11' 36.6"	1720	01/01/2010	31/01/2018
RECOPE, La Garita	10° 00' 19.0"	84° 17' 45.0"	740	12/01/2010	31/01/2018
West Pavas, near to airport	09° 57' 26.3"	84° 08' 51.6"	997	01/01/2010	05/03/2015
Santa Bárbara	10° 02' 00.0"	84° 09' 57.0"	1070	01/01/2010	31/01/2018
Belén	09° 58' 30.0"	84° 11' 08.0"	926	01/01/2010	02/11/2017
Burio hill, Aserrí	09° 50' 25.3"	84° 06' 45.6"	1811	14/11/2012	12/10/2017
Altos Tablazo, Higuito	09° 50' 12.4"	84° 03' 18.1"	1660	28/06/2012	31/05/2017
Chitaria hill, Santa Ana	09° 53' 30.1"	84° 11' 37.3"	1717	01/03/2011	11/10/2017
Poás volcano lake	10° 11' 21.0"	84° 13' 55.2"	2598	05/09/2011	12/02/2018
Cedral hill, Escazú	09° 51' 41.1"	84° 08' 45.2"	2255	29/08/2012	12/10/2017
School of Agricultural Sciences, Santa Lucía, Heredia	10° 01' 22.8"	84° 06' 42.4"	1257	19/11/2013	31/01/2018
West Tobías Bolaños airport, Pavas	09° 57' 26.3"	84° 08' 51.6"	981	05/03/2015	10/10/2017
San Luis	10° 00' 54.0"	84° 01' 36.0"	1341	01/09/2018	31/9/2019
Colima	09° 57' 09.0"	84° 05' 24.2"	1145	01/01/2010	12/31/2017

Table II. Corrosion rate for different corrosivity categories for low carbon steel.

Corrosion category	Corrosion rate ( $\mu\text{m y}^{-1}$ )	Corrosivity level
C1	$\leq 1.3$	Very low
C2	1.3 to 25	Low
C3	25 to 50	Medium
C4	50 to 80	High
C5	80 to 200	Very High
CX	200 to 700	Extreme

In this standard, the set of equations to calculate the corrosion of carbon steel is:

$$\begin{aligned} \text{Vcorr} &= 1.77 P_d^{0.52} \exp(0.020 \text{RH} + f_{st}) + \\ &0.102 S_d^{0.62} \exp(0.033 \text{RH} + 0.040 T), \\ f_{st} &= 0.150(T-10), \quad T \leq 10 \text{ or} \\ f_{st} &= -0.054(T-10), \quad T > 10 \\ N &= 128 \quad R^2 = 0.85 \end{aligned} \quad (3)$$

where,

$f_{st}$ : factor of Steel

Vcorr: corrosion rate in the first year,  $\mu\text{m y}^{-1}$ ,

T: annual average temperature,  $^{\circ}\text{C}$ ,

RH: annual average relative humidity, %,

$P_d$ : annual average  $\text{SO}_2$  deposition,  $\text{mg m}^{-2} \text{d}^{-1}$ ,

$S_d$ : annual average  $\text{Cl}^-$  deposition,  $\text{mg m}^{-2} \text{d}^{-1}$ .

### 2.3. Data processing

Annual averages of RH, T, and TOW were obtained for each location with the corresponding standard deviation. A relatively high correlation between these parameters and altitude (A), in m.a.s.l., was found. The determination correlation coefficient ( $R^2$ ) is a useful statistic for testing linearity. An acceptable value of  $R^2$  must be higher than 0.75 (Wilks, 2011).

General data analysis was performed with Python. The corrosion rate was determined and represented in two maps. One was generated with a simplified model, and the other with the new method formulated by the ISO 9223:2012 standard. Contour lines for the WCV were taken from the Atlas of Costa Rica with a spatial resolution of 10 m (Ortiz-Malavasi, 2015), and the maps were created with ArcGIS software.

The simplified and the ISO 9223:2012 models were compared between them and against experimental

measurements. The latter were obtained according to the procedures in the ISO 9223:2012, ISO 9225:2012, and ASTM G1-03 (ISO, 2012a; ISO, 2012b; ASTM International, 2017) standards.

### 3. Results and discussion

#### 3.1. Meteorological parameters

Most stations were located below 1500 m.a.s.l. and inside the valley. There were less data points in medium-altitude locations a (1500 m.a.s.l. to 2000 m.a.s.l.), and only three in the most elevated parts (above 2000 m.a.s.l.). The geographical distribution of the meteorological observations was not homogeneous. Data points were scarce in the northern section of the WCV, particularly around the foothills of the Barva volcano.

Figures 2, 3, and 4 represent the relations between temperature, relative humidity, and time of wetness with altitude and their standard deviation.

Based on the information presented in figure 2, the equation that describes the temperature variation between 700 m.a.s.l. and 2600 m.a.s.l. is:

$$T = -0.00680A + 28.61 \quad R^2 = 0.971, \quad (4)$$

where,

T: annual average temperature, °C,

A: altitude, m.a.s.l.

The value of the vertical temperature gradient in the WCV from equation (4) is remarkably similar to the global mean value of  $-6.5 \text{ }^{\circ}\text{C km}^{-1}$  in the lower atmosphere Sendiña-Nadal and Pérez-Muñozuri, 2006). The standard deviation tends to increase with altitude at a rate of 2 % for every 1000 m. This behavior is possibly related to a more significant seasonal variability of temperatures in mountainous regions of the WCV (Solano and Villalobos, 2000). Usually, the standard deviation of temperature in the WCV is less than 0.5°C.

In figure 3, it can be observed that relative humidity increases linearly with an altitude between 700 m.a.s.l. and 2600 m.a.s.l. This relation is expressed as:

$$RH = 0.0129A + 61.54 \quad R^2 = 0.951, \quad (5)$$

where,

RH: annual average relative humidity, %,

A: altitude, m.a.s.l.

At higher elevations, the air usually reaches the saturation point, and clouds may form. In the WCV, relative humidity was near the 100 % value at 2600 m.a.s.l. (Murphy and Hurtado, 2013). Above this altitude, equation (5) is not applicable.

The standard deviation of RH is usually less than 5 %, with a slight tendency to decrease with altitude. In the lowest areas of the valley, the seasonal

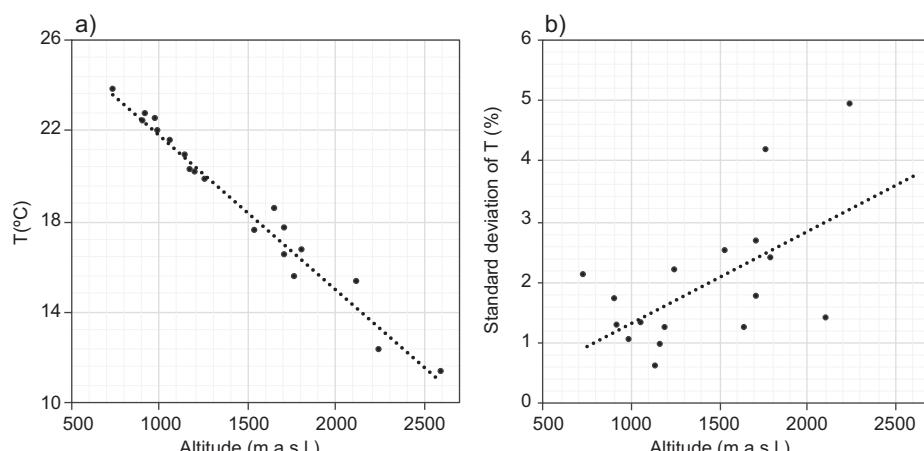


Fig. 2. Variation of (a) annual average and (b) standard deviation of temperature with altitude.

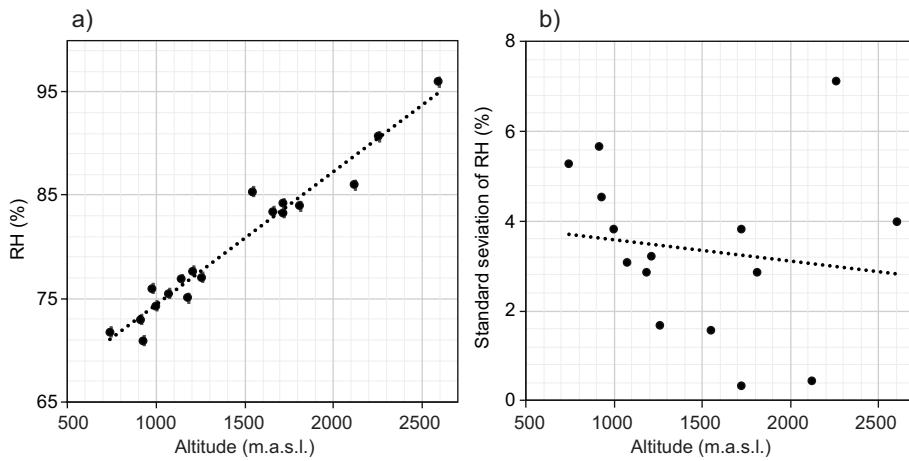


Fig. 3. Variation of (a) annual average and (b) standard deviation of RH with altitude.

variability of RH is usually determined by the differences between dry and rainy seasons (Abdalah-Hernández et al., 2019).

Campos and Castro (1992) explained that RH could quickly vary from 20 % to 100 % at higher elevations of the eastern part of the WCV. This variation is due to dry upper troposphere air and the transport of humid air masses through the mountain pass from the Caribbean region. According to these authors, RH fluctuations decrease at lower elevations.

The relation between time of wetness and altitude from 700 m.a.s.l. to 2600 m.a.s.l., as shown in figure 4, is as follows

$$TOW = 0.000362A + 0.0261 \quad R^2 = 0.900, \quad (6)$$

where,

TOW: average fraction of annual hours of wetness per year, dimensionless,

A: altitude, m.a.s.l.

The TOW increases while the deviation standard decreases with altitude (Rodríguez-Yáñez et al., 2015). This proportionality is due to more saturated air at higher elevations, where RH increases and gets close to 100 %.

The variance of the TOW in the lower valley is associated with changes between the dry and rainy seasons. There is also greater homogeneity in the

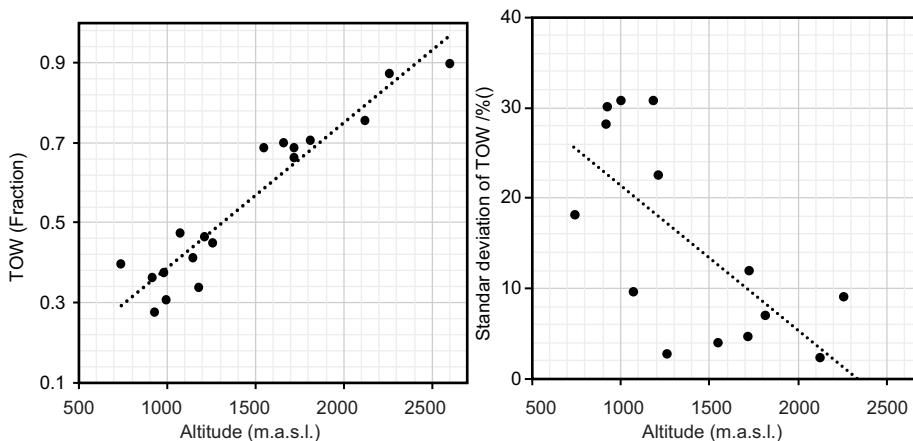


Fig. 4. Variation of (a) annual accumulated average and (b) standard deviation of time of wetness with altitude.

TOW at higher elevations since the RH values tend to be above 80 % for extended periods.

### 3.2. Estimation of Vcorr using the linear and ISO models

Using the linear relationships from the previous section (equations 4 to 6) is possible to calculate the variation of Vcorr with altitude by only considering meteorological variables (equations 1 and 2). The derived equations for corrosion rate, based on RH and TOW, are:

$$V_{\text{corr}} = 0.0083 A + 8.44 \quad R^2 = 0.884, \quad (7)$$

$$V_{\text{corr}} = 0.0123 A + 1.73 \quad R^2 = 0.857 \quad (8)$$

In both cases, the estimated  $R^2$  values are greater than 0.75 and therefore acceptable.

A similar process is applied to the ISO 9223:2012 equation (equation 3). The factors  $P_d$  and  $S_d$  are estimated by Herrera et al. (2012) approximation. In this case:

$$\begin{aligned} V_{\text{corr}} &= 5.861 \exp(0.0006252 A + 0.22586) \\ &+ 0.277 \exp(0.000154 A + 3.175). \end{aligned} \quad (9)$$

$$R^2 = 0.807$$

The simplified equation of ISO 9223:2012 is governed by the effect of RH and increases exponentially with the altitude.

### 3.3. Model output comparison

Field corrosion data was collected from September 2018 to September 2019. Table III shows the location and altitude of the measurement sites, as well as the annual average of the atmospheric variables and pollutants at each point. Atmospheric corrosion, from observations and models (equations 1 to 3 and 7 to 9), is shown in Table IV.

Pollutant levels were similar to those utilized for the approximations with equations 7 to 9; however, RH and TOW did not follow the expected tendency with altitude. The reason for this behavior is probably the position of the stations in the WCV since they were located under the influence of different climatic conditions. Particularly, the station in San Luis is constantly influenced by humid air masses transported from the Caribbean region (Campos and Castro, 1992).

Figure 5 illustrates the predicted corrosion from equations 7 to 9 and their comparison with actual measurements.

The Vcorr values from the simple linear models based on RH and TOW (equations 7 and 8,

Table III. Annual mean atmospheric parameters and levels of pollutants in three different sites.

Site	North latitude	West longitude	A (m.a.s.l.)	RH (%)	TOW (fraction)	T (°C)	$\text{Cl}^-$ ( $\text{mg m}^{-2} \text{d}^{-1}$ )	$\text{SO}_2$ ( $\text{mg m}^{-2} \text{d}^{-1}$ )
CIGEFI	09° 56' 11"	84° 02' 43"	1210	79.92	0.5701	20.29	3.82	6.06
San Luis	10° 00' 54"	84° 01' 36"	1341	90.19	0.8126	18.36	3.52	8.58
Santa Ana	09° 52' 54"	84° 11' 14"	1772	83.46	0.6643	17.41	4.00	7.02

Table IV. Atmospheric corrosion in three different sites, using equations 1 to 3, 7 to 9, and actual values, in  $\mu\text{m y}^{-1}$ . Values in *italics* correspond to overestimations of the corrosion rate compared to actual measurements (bold black quantities). Other modeled corrosion rates showing small differences (less than 5 %) with respect to observations are underlined.

Site	Vcorr model RH (eq. 1)	Vcorr model TOW (eq. 2)	Vcorr ISO 9223 (eq. 3)	Vcorr Observed	Vcorr model RH (eq. 7)	Vcorr model TOW (eq. 8)	Vcorr ISO 9223 (eq. 9)
CIGEFI	19.2	20.8	20.8	<b>17.4</b>	<u>16.7</u>	18.6	23.8
San Luis	28.9	26.5	30.0	<b>17.3</b>	<u>18.2</u>	19.6	25.2
Santa Ana	22.5	22.9	24.9	<b>16.6</b>	23.4	23.2	31.0

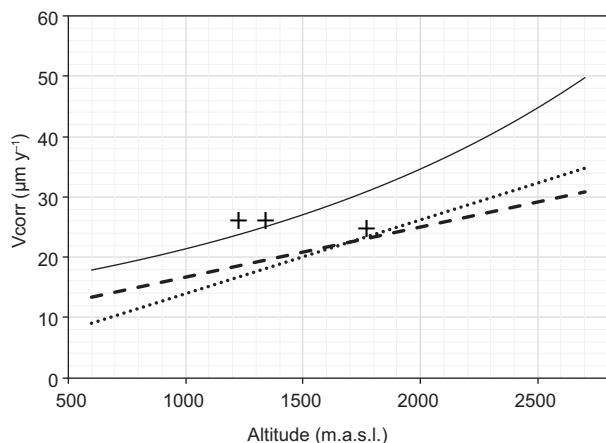


Fig. 5. Vcorr vs. Altitude, for a model using a) equation 7 (RH, dotted line), b) equation 8 (TOW, dashed line), c) equation 9 (ISO 9223, solid line). Actual measurements are represented by cross markers (+).

respectively) increased rapidly with altitude and corresponded to C2 and C3 corrosivity categories, according to the ISO 9223:2012 standard (Table II). The corrosion in the ISO 9223:2012 model shows a more significant increase with altitude. This increase is due to the exponential behavior of equation 9, governed by the RH variable. The difference between observed values and the ISO 9223:2012 equation is around 20 % at medium altitudes. In the mountain (Santa Ana), this contrast reaches the order of 100 %.

Model outputs in comparison with observations presented notable differences. When the atmospheric parameters are used (equations 1 and 2), the deviations are greater in places with high values of *RH* (*RH* > 80 %) or *TOW* (*TOW* > 0.6), for example, in San Luis. When considering the simple models with altitude dependency (equations 7 and 8), there is generally a good estimation of Vcorr in the region between 1000 m.a.s.l. and 1400 m.a.s.l. Overestimation greater than 10% occurs at altitudes higher than 1500 m.a.s.l. It is important to consider that most of the population of the WCV lives within the 900 m.a.s.l to 1400 m.a.s.l altitude range (INEC, 2011).

The model-based of ISO 9223:2012 (equations 3 and 9) presented higher values with respect to observations. This problem was already pointed out in

some studies carried out in the tropical atmosphere (Correa-Bedoya et al., 2007; Corvo et al., 2008, Morcillo et al., 2012; Morcillo et al., 2013, Garita-Arce et al., 2014; Rios et al., 2017; Vera et al., 2017).

In figure 6, the shown maps complement each other. It is possible to apply both the RH- and the TOW-based models (Fig. 6a or 6b, respectively) in the central region of the WCV (from 900 m.a.s.l to 1400 m.a.s.l) and the ISO 9223:2012 model (Fig. 6c) overestimated the corrosion in all altitudes.

#### 4. Conclusions

Simple models based on RH, TOW, and the ISO standard were used to determine Vcorr in the WCV. The measurements indicated intermediate (C2) levels of Vcorr in the region, with values ranging from 16.6 to 17.4 µm y⁻¹. Almost all the proposed models presented a level of Vcorr within the C2 category.

The linear equations dependent on atmospheric parameters only (equations 1 and 2) always overestimated the value of Vcorr with differences between 10 % and 70 %. Conversely, the altitude-dependent models (equations 7 and 8), presented a more realistic estimation, between 1000 m.a.s.l and 1400 m.a.s.l.

The equation of the ISO 9223:2012 standard (equation 3) and its simplified form based on the altitude (equation 9) showed an exponential behavior governed by the increase of RH with altitude.

The results demonstrated that linear equations with regular parameters, such as RH, are more practical for determining Vcorr at low altitudes in the WCV, specifically in the range of 1000 m.a.s.l to 1400 m.a.s.l., where most of the population of the WCV lives. Vcorr calculations out of this range showed larger discrepancies with respect to observations (more than 10 %).

The ISO model overestimated the Vcorr values in the WCV for all altitudes. In some cases, the differences were greater than 20 %.

The WCV is not a climatically uniform region, as it shows significant spatial and temporal variations. This variability suggests the need for more assessments considering these factors, given the dependency of corrosion with RH. Future analyses should encompass mountain profiles, climatic sub-regions, and climatic periods (for example, dry and rainy seasons).

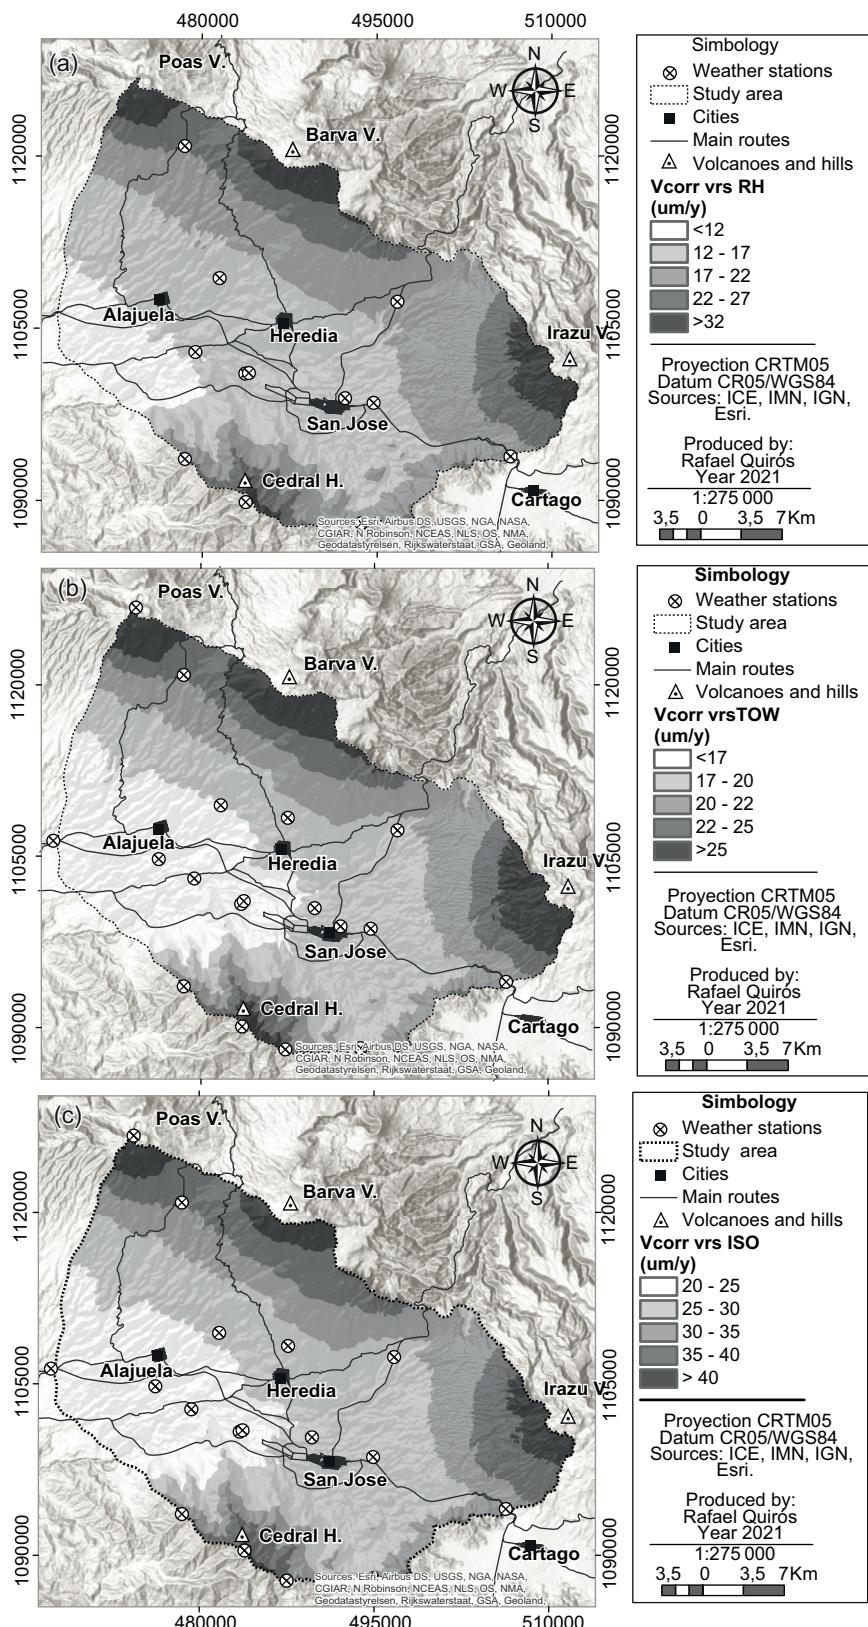


Fig. 6. Map of Vcorr using the a) RH, b) TOW, and c) ISO models.

## Acknowledgments

Special thanks to the National Meteorological Institute and the Costa Rican Electricity Institute for providing the meteorological data of the Western Central Valley. The actual corrosion data was obtained from measuring sites located at facilities of the National Power and Light Company and the Ministry of Security. This study was funded by the National Council of University Presidents (CONARE) of Costa Rica as part of a collaborative project among the State Distance University (UNED-VINVES-6-10-50), the University of Costa (UCR-VI-805-B8-650), the National High Technology Center (CeNAT-VI-269-2017), the National University (UNA-SIA: 0600-17), and the Costa Rica Institute of Technology (ITCR-VIE 1490-021).

Rodríguez-Yáñez acknowledges the support of the Innovation and Human Capital for Competitiveness Program (PINN) of the Ministry of Science, Technology, and Telecommunications (MICITT) of Costa Rica.

## References

- Abdalah-Hernández M, Rodríguez-Yáñez J, Alvarado-González D. 2020. Gaussian mixture analysis of basic meteorological parameters: Temperature and relative humidity. *Tecnología en Marcha* 33:5-12. <https://doi.org/10.18845/tm.v33i5.5068>
- Alcántara J, Chico B, de la Fuente D, Morcillo M. 2015. Airborne chloride deposit and its effect on marine atmospheric corrosion of mild steel. *Corrosion Science* 97:74-88. <https://doi.org/10.1016/j.corsci.2015.04.015>
- Amador J. 2008. The Intra-Americas Sea low-level jet. *Annals of the New York Academy of Sciences* 1146 (1):153-188. <https://doi.org/10.1196/annals.1446.012>
- ASTM International. 2017. ASTM G1-03(2017)e1 Standard Practice for Preparing, Cleaning, and Evaluating Corrosion Test Specimens. American Society for Testing and Materials International. West Conshohocken, PA, USA. <https://doi.org/10.1520/G0001-03R17E01> (accessed 2018 June 20)
- ASTM International. 2019. ASTM A36 / A36M-19 Standard Specification for Carbon Structural Steel. American Society for Testing and Materials International. West Conshohocken, PA, USA. [https://doi.org/10.1520/A0036\\_A0036M-19](https://doi.org/10.1520/A0036_A0036M-19) (accessed 2018 June 20)
- Barrantes J, Liao A, Rosales A. 1985. Atlas climatológico de Costa Rica. San José, Costa Rica: Instituto Meteorológico Nacional. Available at <https://www.imn.ac.cr/atlas-climatologico> (accessed 2019 Jun 12)
- Caetano E, Iniesta R. 2008. Identificación de cuencas atmosféricas en México. Instituto de Ecología y Cambio Climático de México. Available at <https://docplayer.es/58286477-Identificacion-de-cuencas-atmosfericas-en-mexico.html> (accessed 2018 April 15)
- Campos M, Castro V. 1992. El clima a sotavento de las montañas de Costa Rica. *Tópicos Meteorológicos y Oceanográficos* 2:1-21. Available at: <https://hdl.handle.net/10669/551> (accessed 2021 March 3)
- Corvo F, Pérez T, Martín Y, Reyes J, Dzib L, González-Sánchez J and Castañeda A. 2008. Time of wetness in tropical climate: Considerations on the estimation of TOW according to ISO 9223 standard. *Corrosion Science* 50:206-219. <https://doi.org/10.1016/j.corsci.2007.06.012>
- Correa-Bedoya E, Botero-Vega C, Restrepo AH, Delgado J, Castaño JG, Echevarría F. 2007. Corrosión del acero al carbono, acero galvanizado y aluminio en diferentes atmósferas colombianas. *Scientia et Technica*, 13(36): 7-12.
- Díaz I, Cano H, Lopesino P, de la Fuente D, Chico B, Jiménez J, Medina SF, Morcillo M. 2018. Five-year atmospheric corrosion of Cu, Cr and Ni weathering steels in a wide range of environments. *Corrosion Science* 141:146-157. <https://doi.org/10.1016/j.corsci.2018.06.039>
- Feliu S, Morcillo M, Feliu S. 1993. The prediction of atmospheric corrosion from meteorological and pollution parameters. I. Annual corrosion. *Corrosion Science* 34:403-4014. [https://doi.org/10.1016/0010-938X\(93\)90112-T](https://doi.org/10.1016/0010-938X(93)90112-T)
- Fernández W, Campos M, Amador JA. 2003. Second progress report of the AIACC LA06 project: Assessment of impacts and adaptation measures for the water resources sector due to extreme events under climate change conditions in Central America. AIACC. Available at [https://sedac.ciesin.columbia.edu/aiacc/progress/LA06\\_July03.pdf](https://sedac.ciesin.columbia.edu/aiacc/progress/LA06_July03.pdf) (accessed 2019 June 11)
- García-Reynoso JA, Ruiz-Suárez LG, García-Escalante JS, Reséndiz-Juárez NA. 2009. Comportamiento de los contaminantes en cuencas atmosféricas: Metodología y estudio de caso (INE/A1-004/2009), Mexico: INE.
- Garita-Arce L, Rodríguez-Yáñez J, Robles-Cordero J. 2014. Modelado de la velocidad de corrosión de

- acero de baja aleación en Costa Rica. Revista Ingeniería 24:79-90. <https://doi.org/10.15517/RING.V24I2.14624>
- Herrera-Murillo J, Rodríguez S, Rojas-Marín J, Báez A. 2012. Relations between bulk precipitation, PM10 composition and meteorological conditions in the metropolitan area of Costa Rica. The Open Journal of Atmospheric Sciences 6:19-32. <https://doi.org/10.2174/1874282301206010019>
- Herrera J, Rojas JF, Beita VH, Chaves M. 2014. Composición química de muestras de deposición total colectadas en el área metropolitana de Costa Rica en 2012. Ciencias Ambientales 48:30-38. <https://doi.org/10.15359/rca.48-2.3>
- IMN. 2008. Clima, variabilidad y cambio climático en Costa Rica. San José, Costa Rica: Comité Regional de Recursos Hídricos. Available at <http://cglobal.imn.ac.cr/documentos/publicaciones/CambioClimatico/climaVariabilidadCambioClimaticoCR.pdf> (accessed 2019 April 17)
- INEC. 2011. Anuario estadístico 2010. San José, Costa Rica: Instituto Nacional de Estadística y Censos, Ministerio de Hacienda. Available at [https://www.inec.cr/sites/default/files/documentos/anuario\\_estadistico/publicaciones/reanuarioestad2010-02.pdf](https://www.inec.cr/sites/default/files/documentos/anuario_estadistico/publicaciones/reanuarioestad2010-02.pdf) (accessed 2019 May 27)
- ISO. 1992. Corrosion of metals and alloys - Corrosivity of atmospheres - Classification (ISO 9223:1992). ISO. Available at <https://www.iso.org/standard/16855.html> (accessed 2018 June 20)
- ISO. 2012a. Corrosion of metals and alloys - Corrosivity of atmospheres - Classification, determination and estimation (ISO 9223:2012). ISO. Available at <https://www.iso.org/standard/53499.html> (accessed 2018 June 20)
- ISO. 2012b. Corrosion of metals and alloys – Corrosivity of atmospheres – Measurement of pollution (ISO 9225:2012). ISO. Available at <https://www.iso.org/standard/53501.html> (accessed 2018 June 20)
- Magaña V, Amador JA, Medina S. 1999. The mid-summer drought over Mexico and Central America. Journal of Climate 12 (6):1577-1588. [https://doi.org/10.1175/1520-0442\(1999\)012<1577:TM-DOMA>2.0.CO;2](https://doi.org/10.1175/1520-0442(1999)012<1577:TM-DOMA>2.0.CO;2)
- Morcillo M, Almeida E, Rosales B, Uruchurtu J, Marrocos M. 1998. Corrosión y protección de metales en las atmósferas de Iberoamérica. Parte I: Mapas iberoamericanos de corrosión atmosférica (MICAT). Madrid, Spain: CYTED.
- Morcillo M, De la Fuente D, Díaz I, Cano H. 2011. Atmospheric corrosion of mild steel. A review. Revista Metalurgia 47: 426–444. <http://doi.org/10.3989/revmetalm.1125>
- Morcillo M, Chico B, de la Fuente D, and Simancas J. 2012. Looking back on contributions in the field of atmospheric corrosion offered by the MICAT Ibero-American testing network. International Journal of Corrosion 2012:1-24. <https://doi.org/10.1155/2012/824365>
- Morcillo M, Chico B, Díaz I, Cano H, de la Fuente D. 2013. Atmospheric corrosion data of weathering steels. A review. Corrosion Science 77:6-24. <https://doi.org/10.1016/j.corsci.2013.08.021>
- Morcillo M. 2017. Fundamental and research frontier of atmospheric corrosion. Materials, Madrid, Spain. <https://doi.org/10.3390/books978-3-03842-642-4>
- Muñoz AC, Fernández W, Gutiérrez JA, Zárate E. 2002. Variación estacional del viento en Costa Rica y su relación con los regímenes de lluvia. Tópicos meteorológicos y oceanográficos 9: 1-13.
- Murphy GM, Hurtado, RH. 2013. Agrometeorología. Buenos Aires, Argentina: Editorial Facultad de Agronomía, Universidad de Buenos Aires. 57-70.
- NOAA. 2019. Cold and warm episodes by season. National Weather Service of the United States. Available at: [http://origin.cpc.ncep.noaa.gov/products/analysis\\_monitoring/ensostuff/ONI\\_v5.php](http://origin.cpc.ncep.noaa.gov/products/analysis_monitoring/ensostuff/ONI_v5.php) (accessed 2019 October 27)
- Ortiz-Malavasi E. 2015. Atlas digital de Costa Rica 2014. Instituto Tecnológico de Costa Rica. Cartago, Cartago, Costa Rica. Available at <http://hdl.handle.net/2238/7477> (accessed 2019 July 25)
- OVSICORI. 2015. Estado de los volcanes. Observatorio Vulcanológico y Sismológico de Costa Rica. Available at <http://www.ovsicori.una.ac.cr/index.php/extension/estado-de-los-volcanes> (accessed 2019 October 21)
- Ríos-Rojas JF, Aperador-Rodríguez D, Hernández-García EA, Arroyave-Posada CE. 2017. Annual atmospheric corrosion rate and dose-response function for carbon steel in Bogotá. Atmósfera 30:53-61. <https://doi.org/10.20937/atm.2017.30.01.05>
- Roberge PR, Klassen RD, Haberecht PW. 2002. Atmospheric corrosivity modeling-A review. Materials and Design 23:321-330. [https://doi.org/10.1016/S0261-3069\(01\)00051-6](https://doi.org/10.1016/S0261-3069(01)00051-6)
- Robles J. 2013. Evaluation of atmospheric corrosion in three geographic areas of Costa Rica by electrochemical and gravimetric techniques. Bachelor thesis, Universidad Nacional de Costa Rica.

- Rodríguez-Yáñez JE, Garita-Arce L, Saborío-Leiva E. 2015. Mapas estimativos de la corrosión atmosférica de acero de baja aleación en Costa Rica. Cuadernos de Investigación 7:181-191. <https://doi.org/10.22458/urj.v7i2.1144>
- SEMARNAT-INECC. 2016. Diagnóstico sobre la calidad del aire en cuencas atmosféricas de México. Instituto de Ecología y Cambio Climático de México. Mexico City, Mexico. Available at: <http://biblioteca.semarnat.gob.mx/janium/Documentos/Ciga/Libros2013/CD002516.pdf> (accessed 2019 January 17)
- Sendiña-Nadal I, Pérez-Muñozuri, V. 2006. Fundamentos de meteorología. Galicia, Spain: Universidad Santiago de Compostela.
- Solano J., Villalobos R. (2000). Regiones y subregiones climáticas de Costa Rica. Instituto Meteorológico Nacional de Costa Rica. Available at: <https://www.imn.ac.cr/documents/10179/20909/Regionalizaci%C3%B3n+clim%C3%A1tica+de+Costa+Rica> (accessed 2018 January 17)
- Nacional de Costa Rica. Available at: <https://www.imn.ac.cr/documents/10179/20909/Regionalizaci%C3%B3n+clim%C3%A1tica+de+Costa+Rica> (accessed 2018 January 17)
- Vera R, Troconi de Rincón O, Bagnara M, Romero N, Araya R, Ossandón S. 2017. Tropical/non-tropical marine environments impact on the behaviour of carbon steel and galvanised steel. Materials corrosion 69:614-625. <https://doi.org/10.1002/maco.201709873>
- Wilks DS. 2011. Statistical Methods in the Atmospheric Sciences. United States: Academic Press.
- Zárate E. 1978. Comportamiento del viento en Costa Rica. Nota técnica de investigación Nº 2. Instituto Meteorológico Nacional de Costa Rica.
- Zárate E. 1980. El viento en San José. Instituto Meteorológico Nacional de Costa Rica.