

Artículo original
(Original paper)

**MECHANICAL CHARACTERIZATION OF THE AMAZONIAN *POMACEA DOLIOIDES*
(REEVE, 1856) SHELL**

**CARACTERIZACIÓN MECÁNICA DE CONCHAS AMAZÓNICAS DE *POMACEA DOLIOIDES*
(REEVE, 1856)**

ARIANA FREIRE ANDRADE*, RODRIGO BÍSCARO NOGUEIRA

Instituto de Ciências Exatas e Tecnologias - ICET, Universidade Federal do Amazonas –UFAM, Rua Nossa Senhora do Rosário, 3863, Tiradentes. CEP: 69103-128, Itacoatiara, Amazonas, Brazil. <rodrigobiscaro@gmail.com>

*Corresponding author: <arianaandrade01@hotmail.com >

Recibido: 01/09/2017; aceptado: 15/03/2018; publicado en línea: 29/10/2018
Editor responsable: Alfonso Correa Sandoval

Andrade, A. F., Nogueira, R. B. (2018) Mechanical characterization of the Amazonian *Pomacea dolioides* (Reeve, 1856) shell. *Acta Zoológica Mexicana (nueva serie)*, 34, 1–11. DOI: <https://doi.org/10.21829/azm.2018.3412120>

ABSTRACT. We investigated the mechanical behavior of freshwater mollusk shells, *Pomacea dolioides*, collected from a floodplain area located in Amazonas, Brazil. With the purpose of characterizing the mechanical properties of the shells, bending, hardness and roughness tests were carried out. To determine the shell flexural strength, a new methodology was proposed for the calculation of it, considering the curved geometry of the specimens taken from the shells. It was also described the mechanical properties as a function of shell position and thickness, variation of the surface hardness along the shell and the low level of superficial irregularity in the inner layer of the shells. Shell presented a mean flexural rupture modulus (MOR) of 128.0 MPa, Rockwell HR_{15N} hardness = 50 ± 8.3 and a low level of irregularities in the inner layer, roughness Ra = 0.160 µm.

Key-words: *Pomacea dolioides*; mechanical properties; flexural strength; hardness; houghness

Andrade, A. F., Nogueira, R. B. (2018) Caracterización mecánica de conchas amazónicas de *Pomacea dolioides* (Reeve, 1856). *Acta Zoológica Mexicana (nueva serie)*, 34, 1–11. DOI: <https://doi.org/10.21829/azm.2018.3412120>

RESUMEN. Investigamos el comportamiento mecánico de las conchas de moluscos de agua dulce, *Pomacea dolioides*, recolectados en un área de llanuras aluviales en Amazonas, Brasil. Con el fin de caracterizar las propiedades mecánicas de éstas, se utilizaron ensayos de flexión, dureza y rugosidad. Para determinar la resistencia a la flexión del material, se propuso una nueva metodología para el cálculo de la resistencia a la flexión, considerando la geometría curva de los cuerpos de prueba retirados de las conchas. También se describieron las propiedades mecánicas analizados en función de la posición y de la espesura de la concha, la variación de la superficie de la rigidez con el concha y el nivel bajo de irregularidad superficial en la superficie interna de las conchas. La concha presentó el Módulo de Ruptura a la Flexión (MOR) medio de 128.0 MPa, dureza superficial Rockwell HR_{15N} = 50 ± 8.3 y un bajo nivel de irregularidades en la capa interna, con rugosidad Ra = 0.160 µm.

Palabras clave: *Pomacea dolioides*; propiedades mecánicas; fuerza flexible; dureza; rugosidad



INTRODUCTION

Several biological materials attract attention due to the unique mechanical resistance properties and singular structures that they present, even though they are constituted for the most part by minerals, which when considered in isolation, can present great fragility (Chen *et al.*, 2008). However, when associated with organic matrices, they form hybrid composites of a ceramic and a biopolymer with microarchitecturally different sections and structures highly organized with extraordinary mechanical properties as those found in mollusks shells (Sarıkaya & Aksay, 1992; Graham & Sarıkaya, 2000; Lin *et al.*, 2006; Chen *et al.*, 2008; Heinemann, 2011).

Shells are remarkable structures of biological origin, with unique shapes and designs, and for some mollusks, properties such as superior fracture resistance, flexural strength and hardness (Currey & Taylor, 1974; Cortie *et al.*, 2006; Shojaei *et al.*, 2012). Such hard exoskeleton has great importance for animals living in tropical and humid environments, even though they are made up of thin structures, provide support and protection against predators, mechanical damage, dehydration and hydrostatic pressure (Furuhashi *et al.*, 2009; Francis, 2012; Watanabe *et al.*, 2015; Morii *et al.*, 2016).

Many organisms, among them mollusks, have developed sophisticated strategies to direct the growth of the inorganic constituents of their mineralized matter, resulting in improvements in mechanical properties. Many researchers study this characteristic in order to apply the same biomineralization strategies in synthetic materials development as composite materials and materials for medical applications (Volkmer, 2000; dePaula *et al.*, 2010; Putro *et al.*, 2014; Yao *et al.*, 2015). In this context, the genus *Pomacea* Perry, 1810, considered the largest group of freshwater gastropods, with approximately 20 species registered for the Amazon Region, among them *Pomacea dolioides* (Reeve, 1856) (Simone, 2006), is considered important in the development of new composite materials.

The gastropods of the genus *Pomacea* have already been studied for various aspects, antipredator behavior (Ueshima & Yusa, 2014), temperature effects on the shells (Yoshida *et al.*, 2013; Bae & Park, 2015) the environment effects on shell shapes (Estebenet & Martín, 2003) effects of its introduction into other environments (Rawlings *et al.*, 2007; Horgan *et al.*, 2014) reproduction (Estoy Jr *et al.*, 2002; Barnes *et al.*, 2008; Wu *et al.*, 2011) and its behavior in Amazon floodplain areas (Watanabe *et al.*, 2015; Fonseca *et al.*, 2017). However, even a shell being a structure of extreme importance for maintaining the animal life in its natural habitat, it was not found information regarding the behavior of this genus shells when subjected to mechanical stresses resulting from natural impacts, predator attacks and other abrasive effects of the environment.

The present study aimed to analyze the mechanical behavior of *P. dolioides* (Reeve, 1856), seeking to characterize the mechanical properties that confer protection to the mollusk. The resistance to the three-point bending is directly related to the load supported by the shell until the fracture, while the hardness may be related to the shell resistance to the wear provided by the environment and may present variations in the different shell layers due to the porosity, presence of organic phase and microstructural characteristics. The surface roughness of the shell, can provide information of the capacity of sliding of the animal in the shell and also of the inter-lamellar sliding of the microstructure, due to the nano-asperities present in the crystals microconstituents (Graham & Sarıkaya, 2000; Evans *et al.*, 2001; Wang *et al.*, 2001; Liang *et al.*, 2008; Yang *et al.*, 2011; Lv *et al.*, 2015; Liang *et al.*, 2016).

MATERIALS AND METHODS

Shells used. In order to perform all the experiments described, one hundred empty shells of *P. dolioides* of different sizes were collected from a floodplain area located in Itacoatiara (AM), Brazil (03°08'24.50"



S, 58°27'24.60" W), in the mid Amazon region, between June and August 2016. The shells were washed in running water with detergent, dried and kept at room temperature during the experiments. The Mollusca Collection of the Oswaldo Cruz Institute (CMIOC) carried out the specie identification, with the register number CMIOC 10552: *Pomacea dolioides* (Reeve, 1856).

Bending test

In order to analyze the strength of *P. dolioides* shells, a three-point bending test was carried out with some shells specimens. The method consists of applying a load (P) in the central area of a standardized specimen supported at its ends, thus generating flexion, as shown in Figure 1 a) and b).

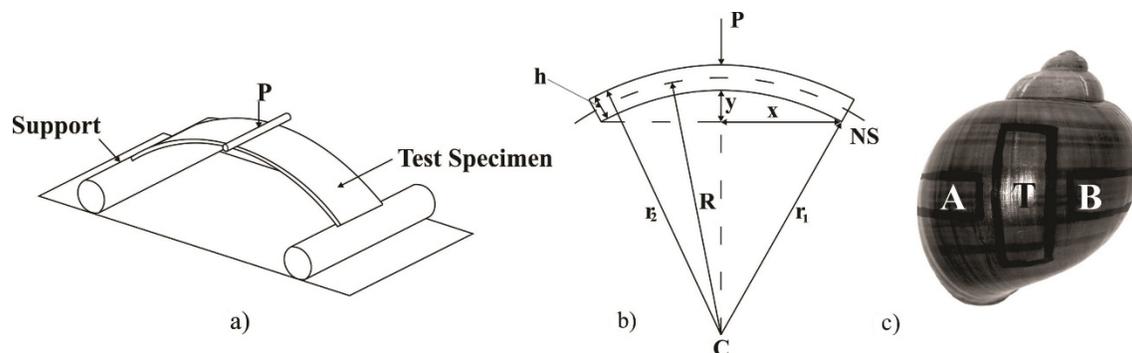


Figure 1. a) Illustration showing the specimen with two points of support and a load application point. b) Representation of the curved specimen, showing its center of curvature (C) Neutral surface (NS), applied load (P) and distances: R , r_1 , r_2 , y , h e x . c) Shell of *P. dolioides*, showing positions A, T and B from where the specimens were withdrawn.

Tests were carried out in compliance with the American Society for Testing Materials (ASTM) C1161-13 for ceramic materials; however, some adjustments in the test were necessary due to the impossibility to withdraw specimens in straight prism format rectangles. The test was performed at room temperature, with a distance between supports of $x = 40.0$ mm ($x = 20.00$ mm).

Only shells larger than 40 mm could be used in bending tests, since the small shells were not large enough for the extraction of test specimens with adequate dimensions for the test.

Specimens for the bending test were taken from three different shell positions: next to the open and transversal direction (ID: A), central area and longitudinal direction (ID: T) and opposite area and cross direction (ID: B), as shown in Figure 1c). The specimens were cut from the shell using a disc and measured using a caliper rule Digimess. The mean width (W_m) and the mean thickness (h_m) were obtained by the arithmetic mean of five points measured along the specimen.

The calculation of the flexural strength of the shell material was performed using two methods: the first one calculates the Flexural Rupture Module (MOR) using Equation 1, where (P) is the maximum load applied to the specimen until its rupture and (x) is the arm of the bending moment, distance from the application of the load to the bearing, as described in Technical Standard ASTM C1161-13. The second method used to calculate the flexural strength sought to correct the effects of the shell curvature in the calculation of the MOR described by Technical Standard ASTM C1161-13, since the specimens of the *P. dolioides* should be treated as a curved beam, not as a prism recto rectangle.

The second method proposed in this work aims to obtain the tensile stress (σ_t), maximum stress on the lower surface of the specimen in the region of load application, and the compression stress (σ_c), minimum (negative) stress on the upper surface of the specimens in the region of load application, using

Equations 2 and 3, respectively, in which the specimen curvature is considered. In equations 2 and 3, the bending moment (M) was obtained through Equation 4, the mean radius (r_m) was calculated by means of the arithmetic mean of the internal (r_1) and external (r_2) rays, Equation 5, the radius (R) from the Center of Curvature (C) to the Neutral Surface (NS) was obtained using Equation 6, where (A) is the cross-sectional area of the specimen. And for the calculation of (r_2), we used Equation 7.

The geometric relationship between parameters (x), (y) and (r_1) shown in Figure 1(b) was necessary and it was obtained through the Pythagorean Theorem, as shown in Equation 8.

$$MOR = \frac{3P \cdot 2x}{2w_m h_m^2} \quad (1)$$

$$\sigma_t = \frac{M(r_2 - R)}{A(r_m - R)r_2} \quad (2)$$

$$\sigma_c = \frac{M(r_1 - R)}{A(r_m - R)r_1} \quad (3)$$

$$M = P \cdot x \quad (4)$$

$$r_m = \frac{1}{A} \int_{r_1}^{r_2} r dA = \frac{r_1 + r_2}{2} \quad (5)$$

$$R = \frac{A}{\int \frac{dA}{r}} = \frac{h}{\ln \frac{r_2}{r_1}} \quad (6)$$

$$r_2 - r_1 = h_m \quad (7)$$

$$r_1 = \frac{y^2 + x^2}{2y} \quad (8)$$

Rockwell Surface Hardness Test. The hardness test was carried out using a Digimes Rockwell durometer, model 400.001 (MSM). The Rockwell Superficial hardness scale 15N (HR_{15N}) was used with a diamond indenter with 3.00 kgf preloading and a 15.00 kgf main load. Forty (40) tests on shells with four (4) different sizes were performed. The specimens analyzed were cut with a circular cutting disc.

Roughness Test. In order to assess the roughness level of the inner layer of the *P. dolioides* shells, the test was carried out using an Instrutherm Digital Surface Roughness Tester RP-200. The parameters calculated through this mechanical test followed the standard method of the International Organization for Standardization (ISO) standard ISO 4287, considering a 0.25 mm Cut off and a Cut off number equal to 5; an RC ripple filter, a $\pm 40 \mu\text{m}$ Range, a 5 μm diamond needle tip radius, and a 4 mN applied force. To perform the roughness test and optical microscopy (Lumen NIM-100), samples whose internal surface was fairly flat were chosen. The samples used did not undergo any kind of surface treatment, were only washed, dried and kept at room temperature.

Due to the sensitivity of the rugosimeter, it was only possible to perform the test on the inner surface of the shell with no apparent signs of wear since the surfaces that were heavily worn by the environment or the external surface of the shell presented roughness levels outside the scale of the equipment.

RESULTS

Bending test. The results of the bending test of *P. dolioides* shells are presented in Figure 2, showing the flexural rupture modulus (MOR) according to ASTM C1161-13 (black columns) and maximum tensile strength (σ_t) on the lower surface of the specimen following a proposed methodology correcting the



effects of the curved geometry (blank columns). A slight difference between two methodologies is observed, in which the effect of the curved geometry provides a slight increase in the flexural strength of specimens extracted from the shell.

The behavior of MOR as a function of the shell thickness is shown in Figure 3, which shows that the flexural strength of the specimens extracted from *P. dolioides* shells does not have a clear dependence on the shell thickness.

The variation between averages of the results obtained from the bending tests performed on nine specimens drawn from three different shells, considering the positions T, A and B (as shown in Figure 1c) are presented in Figure 4, the standard deviation in relation to the mean is presented as an error bar. It was possible to verify a strong influence on the mechanical properties as a function of the direction and position in which the specimens were removed from the shells.

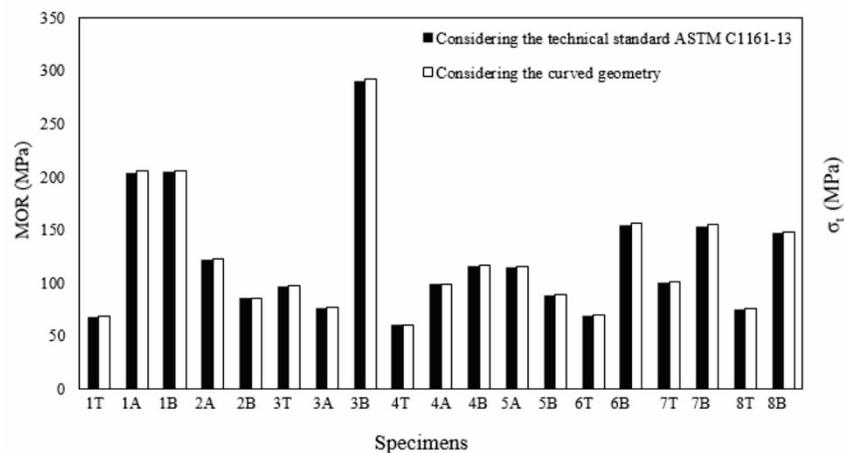


Figure 2. Flexural rupture modulus (MOR) for different test specimens taken from positions A, T and B, following the ASTM C1161-13 (black columns) and maximum tensile strength (σ_t) on the lower surface of the specimen considering the influence of curved geometry (blank columns).

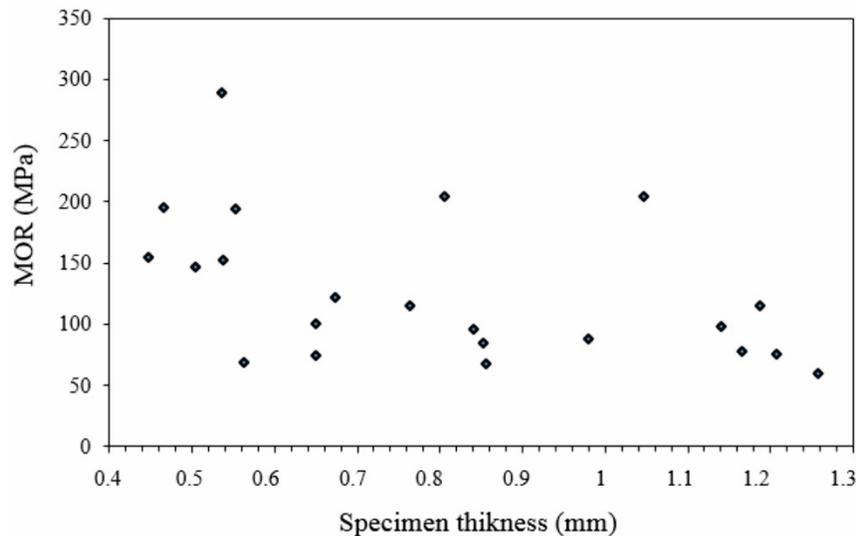


Figure 3. Flexural strength in function of the specimen thickness of *P. dolioides* shells.

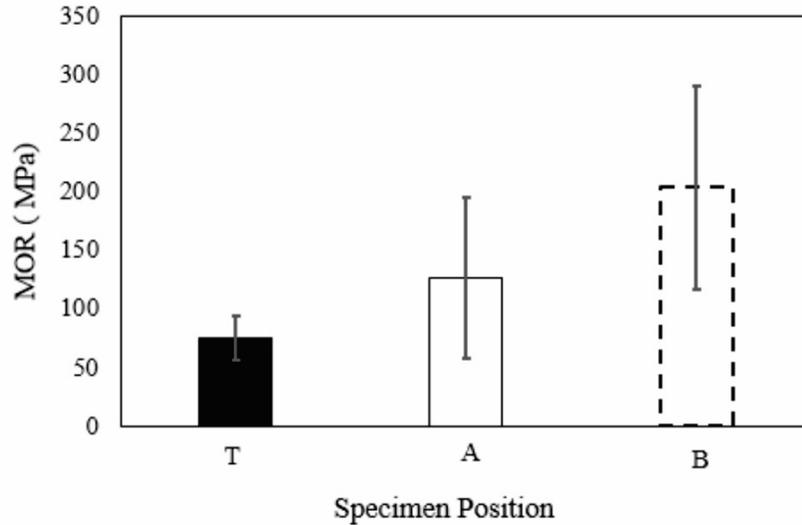


Figure 4. MOR for nine specimens drawn from three different shells, showing the influence of the specimen removal position (T, A and B positions) on flexural strength.

Rockwell surface hardness test. The tests were carried out only in the shell inner layer, since it was impossible to assess the shell outer layer, due to the difficulty to obtain specimens with suitable plans and sizes for the tests. All tests performed on outer layer shell resulted in specimen fracture. For the inner layer of shells with a thickness greater than 1.0 mm, of all samples analyzed, the mean hardness of $HR_{15N} = 50$ and standard deviation 8.3 were obtained.

Figure 5 shows the Rockwell 15N surface hardness behavior of the analyzed shells for three different regions of the shell (close to the suture, center and opposite) and two shell sizes (82.45 mm and 78.05 mm), where the standard deviation from the mean is presented as an error bar, showing a tendency of the region close to the suture in presenting greater hardness HR_{15N} .

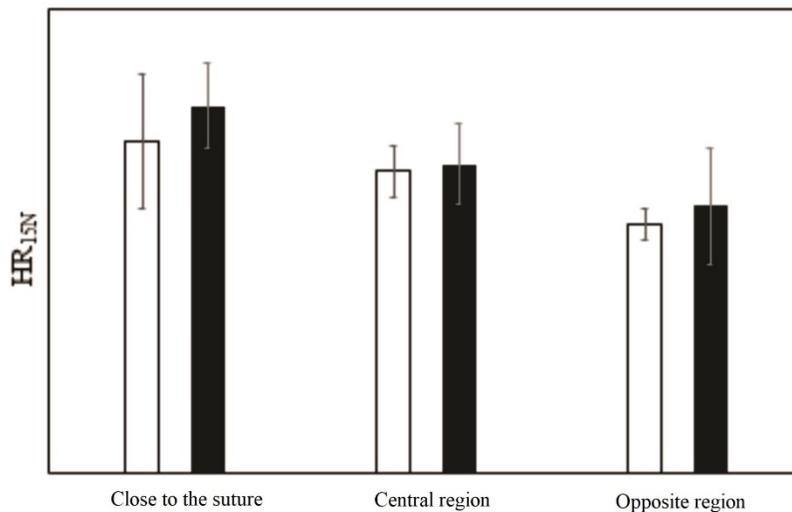


Figure 5. Hardness HR_{15N} of shells with average sizes of 82.45 mm (white) and 78.05 mm (black) in three different regions of the shell (close to the suture, central and opposite) for tests performed in triplicate.



Roughness Test. Roughness is a surface property of the material that characterizes surface irregularity. *P. dolioides* has great irregularity on its external surface, due to the characteristics of the growth rings added to the effect of environmental factors that can generate imperfections on the external surface, which can be clearly seen.

In relation to the shell inner layer, its surface shows a very low roughness index, as long as it has not undergone environmental damage after the death of the mollusk, as can be seen in Table 1, which shows roughness parameters such as the average roughness and the mean roughness amplitude, respectively 0.160 μm and 0.779 μm .

Table 1. Roughness parameters found in the test performed on the inner layer of a shell without signs of environmental wear: average roughness (Ra), square root of the arithmetic mean of squared deviations (Rq), average roughness of five points of the distances between the maximum peaks and deepest valleys (Rz), total roughness depth (Rt), maximum depth of the highest peak relative to the midline (Rp), maximum depth of the deepest valley over the midline (Rv) and maximum roughness (Ry).

Roughness parameters	Measure (μm)
Ra	0.160
Rq	0.182
Rz	0.779
Rt	0.779
Rp	0.300
Rv	0.479
Ry	0.779

The roughness of the inner layer of *P. dolioides* is greatly affected by the action of the environment. Degraded shells show great roughness on the inner surface, as can be seen in the optical microscopy image of the inner layer of the shell Figure 6, with and without apparent signs of environmentally induced surface wear, Figure 6 a and b, respectively.

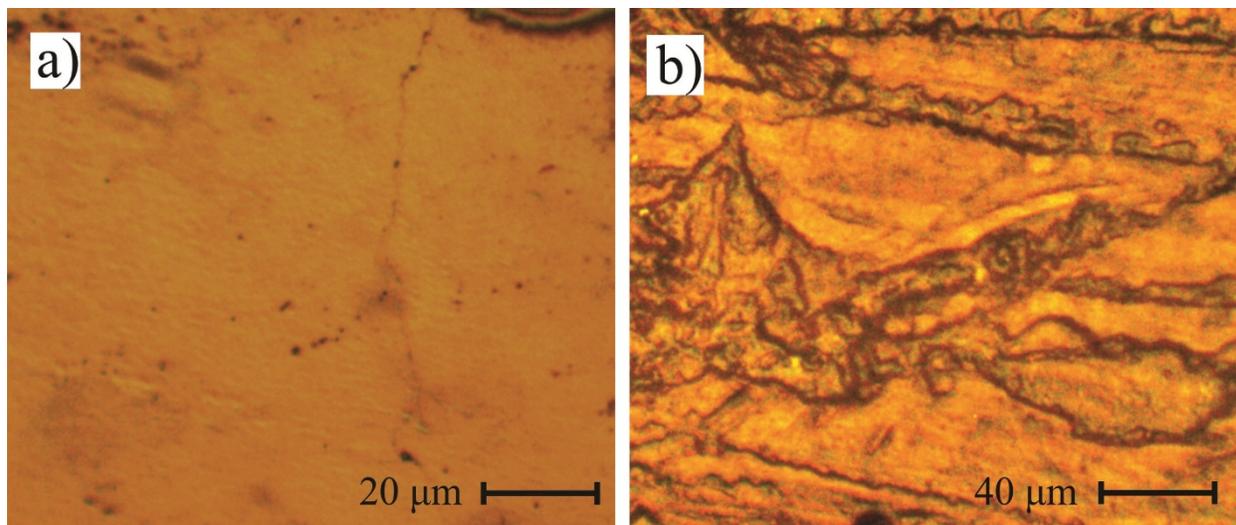


Figure 6. Optical microscopy image of the inner layer surface of *P. dolioides* shells. **a)** No apparent signs of wear caused by the environment. **b)** Signs of surface wear caused by the environment.

DISCUSSION

The mechanical behavior analysis and discussion of *P. dolioides* shells is somewhat complex due to two main factors: the geometric shape and the heterogeneity of the natural shell material (Shojaei *et al.*, 2012). The non-uniformity of the curvatures and the variations in the thickness of the shell make it difficult to remove standardized specimens. The heterogeneity of the shell forming composite due to differences in thickness and composition of the constituent layers of the shell generates anisotropy in the material (Liang *et al.*, 2008). Added to these factors are the presence of defects, imperfections and even cracks in the shell, as well as genetic and environmental factors that may contribute to the variations in the mechanical resistance of the shell.

Bending test. The methodology used to obtain the flexural strength considering the curved shell geometry effect was successful, allowing to accomplish corrections in relation to ASTM C1161-13 standard, and permitting a new manner of flexural behavior analysis of *P. dolioides* specimens, as shown in Figure 2. The analysis of the curved geometry effect on the shell mechanical properties is very important because it directly affects the results of the mechanical tests as discussed in Neves & Mano (2005).

The mean value of MOR = 128.0 MPa, with values varying in range of 60 - 205 MPa, can be compared to the values presented for mollusks such as *Conus striatus* with flexural strength values ranging from 70-200 MPa (Curry & Kohn, 1976) and maximum flexural strength obtained for *S. purpuratus* shells (128 MPa), *Tridacna gigas* shells (87.1 MPa) and *Tridacna maxima* shells (117 MPa) (Liang *et al.*, 2016). Currey & Taylor (1974) also found approximate values as 125 MPa for *Conus Prometheus*, 129.8 MPa for *Hyriu ligutus* and 123.6 MPa for *Etisis siquillu*.

Although large shells withstand higher loads, Figure 3 shows that MOR, the intrinsic property of the material, does not increase with thickness, instead, it presents a tendency of decrease the flexural strength with the increase of shell thickness.

Figure 4 shows a higher flexural strength (MOR) for specimens taken from positions A and B, where the specimens showed growth rings in the transverse direction with respect to their length, and lower MOR for position T, wherein the growth rings were in the direction along the length of the specimen. This result exposes the great anisotropy of the shell forming material, showing that the microstructural composite of CaCO₃ constituent of the shell has great directional effect on the mechanical properties (Liang *et al.*, 2008; Jiao *et al.*, 2016).

The inner layer hardness of *P. dolioides* shells, $HR_{15N} = 50 \pm 8.3$, can even be compared to mollusks that have nacre in the inner layer, such as *Pinctada maxima* (Jameson 1901), *Modiolus modiolus* (Linnaeus, 1758) and *Neotrigonia margaritacea* (Lamarck, 1804), presenting a micro-hardness Vickers (HV) value near to 230 kgf / mm² ($\approx HR_{15N} = 68$) (Taylor and Layman, 1972). Values similar to natural calcite 2.27 GPa (231 kgf / mm² $\approx HR_{15N} = 68$) (Lv *et al.*, 2015). While *Saxidomus purpuratus* presented higher Vickers hardness values for the inner layer, 2.7 GPa (275 kgf / mm² $\approx HR_{15N} = 71$) and central layer, 2.4 GPa (244 kgf / mm² $\approx HR_{15N} = 69$) and lower for the outer layer 1.2 GPa (122 kgf / mm² $\approx HR_{15N} = 58$) (Yang *et al.*, 2011).

The dispersion of the internal layer HR_{15N} values when analyzed in the same region of the shell can be attributed to shell heterogeneity and anisotropy, as well as to the influence of the irregularity of the outer layer (caused by the growth rings) and the shell curvature (Jiao *et al.*, 2016). However, when the shell inner surface hardness is analyzed in relation to the regions of the mechanical tests, there is a tendency of the region close to the suture in presenting greater hardness HR_{15N} , as shown in Figure 5.



The shell abrasion resistance characteristics, which contribute to the protection of the mollusk, are directly related to the shell surface hardness, therefore, it concludes that despite of its organic protective layer, the *P. dolioides* shell is very susceptible to the natural detrition from abrasive materials, such as sand or stones, due to its low surface hardness. This result shows the importance of the shell's regeneration process and reconstitution for the mollusks protection.

Roughness. With the surface roughness test, it was possible to verify that the inner layer shell has a low average surface roughness, $R_a = 0.160 \mu\text{m}$ (Table 1), comparable to a surface with fine grinding or fine polishing. This feature, the low roughness of the shell inner surface, can contribute to the sliding effect of the live animal inside the shell.

The surface roughness data of *P. dolioides* attained can be compared to the variation results of the surface roughness obtained using the technique of atomic force microscopy of growing edge of the mollusk (Graham & Sarikaya, 2000) estimated a rough value, $Z_{rms} = (0.71 \pm 0.13) \mu\text{m}$ of the *Haliotis rufescens* inner layer shell, which can be compared to the maximum amplitude value, $R_z = 0.779 \mu\text{m}$, obtained using the rugosimeter.

The roughness test was performed on shell inner surface with no signs of environmental wear, as shown in Figure 6 (a), showing a fairly smooth surface, which is compatible with the roughness parameters found. However, for shells that have already undergone environmental action and showed signs of surface wear, valleys and depressions can be identified on the surface, as can be seen in Figure 6 (b).

Roughness analysis using the rugosimeter was a simple technique to obtain important information about the shell, since the internal surface roughness can be related to the size and distribution of the shell-forming crystalline CaCO_3 microconstituents, which in turn can be related to the mechanical resistance of the shell (Graham & Sarikaya, 2000).

Conclusions

The methodology applied for the flexural test proved adequate for characterization of the mechanical flexural behavior of this type of material, in which the specimen resembles a curved beam, and it is possible to consider the curved geometry effect in the flexural strength calculations of the shell biocomposite.

The shells microstructural composite presents great anisotropy, with directional effect in the mechanical properties, in which the parallel direction to the growth rings presents less flexural strength. In this context, the superficial hardness results also show a tendency of the inner region close to the suture to present higher values of $\text{HR}_{15\text{N}}$.

The results obtained in surface roughness test indicate that the shell inner layer has a low level of roughness, in addition, the roughness analysis using a rugosimeter represents a simple technique to obtain important information about the shell, since the surface roughness may be related to the size and distribution of the shell-forming CaCO_3 crystalline microconstituents, which in turn may be related to the mechanical strength of the shell.

The mechanical behavior analyzed in this work can be used as a parameter for a better understanding of how the shell provides mollusk protection in relation to predator attack, animal defense mechanisms, abrasion and wear provided by the environment.

ACKNOWLEDGEMENTS. The authors would like to thank the ICET/UFAM'S PET Engineering group for the support regarding experiments, the Foundation for Research Support of the State of Amazonas - FAPEAM and Professor Bruno Sant'Anna for orientation and discussion for the study on *P. dolioides*.

LITERATURE CITED

- Bae, M. J., Park, Y. S.** (2015) Characterizing the effects of temperature on behavioral periodicity in golden apple snails (*Pomacea canaliculata*). *Ecological Informatics*, 29, 130–138.
- Barnes, M. A., Fordham, R. K., Burks, R. L., Hand, J. J.** (2008) Fecundity of the exotic apple snail, *Pomacea insularum*. *Journal of the North American Benthological Society*, 27, 738–745.
- Chen, P. Y., Lin, A. Y. M., Lin, Y. S., Seki, Y., Stokes, A. G., Peyras, J., Olevsky, E. A., Meyers, M. A., Mckittrick, J.** (2008) Structure and mechanical properties of selected biological materials. *Journal of the Mechanical Behavior of Biomedical Materials*, 1, 208–226.
- Cortie, M. B., Mcbean, K. E., Elcombe, M. M.** (2006) Fracture mechanics of mollusc shells. *Physica B: Condensed Matter*, 385, 545–547.
- Currey, J. D., Taylor, J. D.** (1974) The mechanical behaviour of some molluscan hard tissues. *Journal of Zoology*, 173, 395–406.
- Currey J. D., Kohn, A. J.** (1976) Fracture in the crossed-lamellar structure of *Conus* shells. *Journal of Materials Science*, 11, 1615–23.
- Estebenet, A. L., Martín, P. R.** (2003) Shell interpopulation variation and its origin in *Pomacea canaliculata* (Gastropoda: Ampullariidae) from Southern Pampas, Argentina. *Journal of Molluscan Studies*. 69, 301–310.
- Estoy Jr, G. F., Yusa, Y., Wada, T., Sakurai, H., Tsuchida, K.** (2002) Size and age at first copulation and spawning of the apple snail, *Pomacea canaliculata* (Gastropoda: Ampullariidae). *Applied Entomology and Zoology*, 37, 199–205.
- Evans, A. G., Suo, Z., Wang, R. Z., Aksay, I. A., He, M. Y., Hutchinson, J. W.** (2001) Model for the robust mechanical behavior of nacre. *Journal of Materials Research*, 16, 2475–2484.
- Fonseca, A. M., Watanabe, T. T., Hattori, G. Y., Sant'Anna B. S.** (2017) Effects of the dry season on two apple snails of the Amazon. In: Sant'Anna B. S. and Hattori G. Y. (Eds.). *Amazonian Apple Snails*. Nova Science Publishers.
- Francis, R. A.** (2012) *A handbook of global freshwater invasive species*. Routledge.
- Furuhashi, T., Schwarzing, C., Miksik, I., Smrz, M., Beran, A.** (2009) Molluscan shell evolution with review of shell calcification hypothesis. *Comparative biochemistry and physiology Part B: Biochemistry and molecular Biology*, 154, 351–371.
- Graham, T., Sarikaya, M.** (2000) Growth dynamics of red abalone shell: a biomimetic model. *Materials Science and Engineering: C*, 11, 145–153.
- Heinemann, F., Launspach, M., Gries, K. Fritz, M.** (2011) Gastropod nacre: structure, properties and growth-biological, chemical and physical basics. *Biophysical chemistry*, 153, 126–153.
- Horgan, F. G., Stuart, A. M., Kudavidanage, E. P.** (2014) Impact of invasive apple snails on the functioning and services of natural and managed wetlands. *Acta Oecologica*, 54, 90–100.
- Huila, M. F. G., Araki, K., Toma, H. E.** (2010) Confocal Raman and electronic microscopy studies on the topotactic conversion of calcium carbonate from *Pomacea lineate* shells into hydroxyapatite bioceramic materials in phosphate media. *Micron*, 41, 983–989.
- Jiao, D., Liu, Z. Q., Qu, R. T., Zhang, Z. F.** (2016) Anisotropic mechanical behaviors and their structural dependences of crossed-lamellar structure in a bivalve shell. *Materials Science and Engineering: C*, 59, 828–837.
- Liang, Y., Zhao, J., Wang, L., Li, F. M.** (2008) The relationship between mechanical properties and crossed-lamellar structure of mollusk shells. *Materials Science and Engineering: A*, 483, 309–312.



- Liang, Y., Zhao, Q., Li, X., Zhang, Z., Ren, L. (2016) Study of the microstructure and mechanical properties of white clam shell. *Micron*, 87, 10–17.
- Lv, J., Jiang, Y., Zhang, D. (2015). Structural and mechanical characterization of *Atrina Pectinata* and freshwater mussel shells. *Journal of Bionic Engineering*, 12, 276–284.
- Morii, Y., Prozorova, L., Chiba, S. (2016) Parallel evolution of passive and active defense in land snails. *Scientific reports*, 6, 35600.
- Neves, N. M., Mano, J. F. (2005) Structure/mechanical behavior relationships in crossed-lamellar sea shells. *Materials Science and Engineering: C*, 25, 113–118.
- Putro, J. N., Handoyo, N., Kristiani, V., Soenjaya, S. A., Ki, O. L., Soetaredjo, F. E., Ju, Y. H., Ismadji, S. (2014) *Pomacea* sp shell to hydroxyapatite using the ultrasound–microwave method (U–M). *Ceramics International*, 40, 11453–11456.
- Rawlings, T. A., Hayes, K. A., Cowie, R. H., Collins, T. M. (2007) The identity, distribution, and impacts of non-native apple snails in the continental United States. *BMC Evolutionary Biology*, 7, 97.
- Sarikaya, M., Aksay I. A. (1992) Case Ed. *Results and problems in cell differentiation in biopolymers*. Springer, Amsterdam. 1, 1–25.
- Simone, L. R. L. (2006) *Land and freshwater molluscs of Brazil: an illustrated inventory on the Brazilian malacofauna, including neighbour regions of the South America, respect to the terrestrial and freshwater ecosystems*. São Paulo: Fundação de Amparo à Pesquisa do Estado de São Paulo (FAPESP).
- Shojaei, M. F., Mohammadi, V., Rajabi, H., Darvizeh, A. (2012) Experimental analysis and numerical modeling of mollusk shells as a three dimensional integrated volume. *Journal of the Mechanical Behavior of Biomedical Materials*, 16, 38–54.
- Taylor, J. D., Layman, M. (1972) The mechanical properties of bivalve (Mollusca) shell structures. *Paleontology*, 15, 73–87.
- Ueshima, E., Yusa, Y. (2015) Antipredator behaviour in response to single or combined predator cues in the apple snail *Pomacea canaliculata*. *Journal of Molluscan Studies*, 81, 51–57.
- Volkmer, D. (2000) *Biom mineralization*. University of Bielefeld, Bielefeld, Germany Copyright, Academic Press.
- Wang, R. Z., Suo, Z., Evans, A. G., Yao, N., Aksay I. A. (2001) Deformation mechanisms in nacre. *Journal of Materials Research*, 16, 2485–2493.
- Watanabe, T. T., Hattori, G. Y., Sant’Anna, B. S. (2015) Activity, substrate selection, and effect of a simulated Amazon flood regime on the behaviour of the apple snail, *Pomacea bridgesii*. *Marine and Freshwater Research*, 66, 815–821.
- Wu, J. Y., Wu, Y. T., Li, M. C., Chiu, Y. W., Liu, M. Y., Liu, L. L. (2011) Reproduction and Juvenile Growth of the Invasive Apple Snails *Pomacea canaliculata* and *P. scalaris* (Gastropoda: Ampullariidae) in Taiwan. *Zoological Studies*, 50, 61–68.
- Yang, W., Kashani, N., Li, X. W., Zhang, G. P., Meyers, M. A. (2011) Structural characterization and mechanical behavior of a bivalve shell (*Saxidomus purpuratus*). *Materials Science and Engineering: C*, 31, 724–729.
- Yao, Z., Ge, L., Ji, X., Tang, J., Xia, M., Xi, Y. (2015) Surface properties studies of bivalve shell waste by the IGC technique: Probing its significant potential application in the polymer industry. *Journal of Alloys and Compounds*, 621, 389–395.
- Yoshida, K., Matsukura, K., Cazzaniga, N. J., Wada, T. (2014) Tolerance to low temperature and desiccation in two invasive apple snails, *Pomacea canaliculata* and *P. maculata* (Caenogastropoda: Ampullariidae), collected in their original distribution area (northern and central Argentina). *Journal of Molluscan Studies*, 80, 62–66.