

## MWCNTs oxidation by thermal treatment with air conditions

Contreras-Navarrete J. J.\*<sup>1</sup>, Granados-Martínez F. G., Domratcheva-Lvova L.<sup>#</sup>, Flores-Ramírez N., Cisneros-Magaña M. R.,  
*Universidad Michoacana de San Nicolás de Hidalgo  
Gral. Francisco J. Múgica S/N, Felicitas del Río, Morelia, Michoacán, México 58030.*

García-González L., Zamora-Pereido L.  
*Centro de Investigaciones en Micro y Nanotecnología, Universidad Veracruzana  
Calzada Ruiz Cortines, 455, Costa Verde, Boca del Rio, Veracruz, México 94294.*

Mondragón-Sánchez M. L.  
*Posgrado en Metalurgia, Instituto Tecnológico de Morelia  
Av. Tecnológico 1500. Lomas de Santiaguito, Morelia, Michoacán, México 58120.  
(Recibido: 5 de Julio de 2015; Aceptado: 18 de Noviembre de 2015)*

A functionalization process has to occur in order to employ carbon nanotubes, generally by using certain types of acids. Multiwalled carbon nanotubes synthetized from benzene and ferrocene were oxidized at different temperatures between 270-600 °C through thermal treatment at atmospheric conditions. Samples were characterized by SEM, EDS, XRD, FTIR and Raman. The weight loss is shown with fluctuations from 0-78% according to different temperature conditions. FTIR analysis demonstrated presence of carbonyl groups and decrease of CH<sub>x</sub>.

**Keywords:** carbon nanotubes; oxidation; carbonyl group

### 1. Introduction

Carbon Nanotubes (CNTs) are a promising material to be used on many innovative applications due to their physical, chemical and mechanical properties [1, 2]. Different researches involving CNTs incorporation to other materials suggest that better results are obtained when an homogenous dispersion occurs [3]. Generally CNTs functionalization enhances regular distribution into the material in order to facilitate the production of different electronic devices. The conventional methods to add functional groups to CNTs require aggressive treatments, using reflux techniques and highly concentrated acids, resulting in multi-step, expensive and non-environmental friendly processes [4-7].

Most general Multi-Walled Carbon Nanotubes (MWCNTs) acid treatments increment carbonyl and carboxyl functional groups concentrations. Hydroxyl groups are the most important on CNTs polymer nanocomposites applications. Blazej *et al.* propose a method to convert carbonyl and lactone groups into hydroxyl groups via sodium tetrahydroborate treatment [5]. Carbon nanotubes are employed also without functionalization like the solid-phase extraction materials for non-covalent compounds [8]. Li *et al.* reported air oxidation process using previously acid treated CNTs and a 480–750 °C temperature range [9]. Dementev *et al.* described single wall carbon nanotubes oxidation using 400-770 °C temperatures. [9, 10].

The aim of this research was multi-walled carbon nanotubes functionalization through thermal treatment at atmospheric exposure, using different temperature ranges. Further oxidized samples analysis was carried out to obtain morphological structure, element percent concentration and functional groups presence according to each temperature.

### 2. Experimental procedure

#### 2.1 Materials and methods

MWCNTs were obtained by Chemical Vapor Deposition (CVD) into an experimental reactor previously developed and described by Gómez *et al.* [11]. Benzene and ferrocene were organic and organometallic precursors. Temperature was 760 °C with 70 ml/min argon flow.

CNTs samples were characterized and divided for subsequent thermal treatment. MWCNTs were set inside a quartz tube and placed into an electric furnace at 270, 300, 350 400, 500 and 600 °C temperatures for 30 minutes. The fully opened quartz tube, with 0.02 m diameter and 0.6 m length, was used in order to allow atmospheric oxygen exchange.

#### 2.2 Characterization techniques

Scanning Electron Microscopy (SEM) and Energy Dispersive Spectroscopy (EDS), with a JEOL JSM-5910LV, analyzed MWCNTs morphology and elemental composition. CNTs infrared absorbance spectrum was registered through a Fourier Transformed Infrared (FTIR) Tensor 27 Bruker in potassium bromide pellets by 4000-400 cm<sup>-1</sup> amplitude with 32 scans. Multiwalled carbon nanotubes average microstructure was studied by X-ray powder diffraction (XRD) in a Bruker D8 Advance diffractometer (Cu K  $\lambda$  = 0.1506 nm, 20  $\leq$  2  $\leq$  80 with 0.0355°/s). MicroRaman DXR Thermo Scientific (solid state laser 532 nm) was used for Raman spectroscopy.

### 3. Results

Oxidized MWCNTs samples below 400 °C, observed in

\* josecontrerasna@gmail.com; # ladamex@yahoo.es

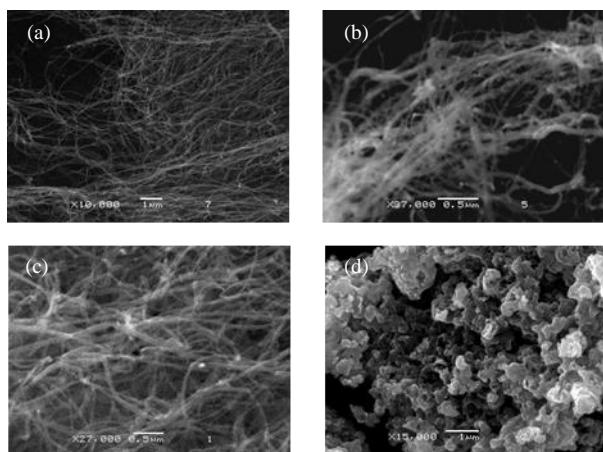


Figure 1. SEM micrographs: (a) Pristine CNTs, oxidized sample at (b) 300 °C, (c) 400 °C, (d) 500 °C.

Figure 1(b, c), resemble to pristine CNTs (Figure 1(a)). However carbon nanotubes were not observed in samples treated above 500 °C (Figure 1(d)). Different element atomic percentages were observed through EDS analysis for treated samples, as shown in TABLE I. Domratcheva *et al.* explained the Fe role in carbon self-organization into CNTs[12].

Atomic element percentage behaves differently according to the oxidation temperature Figure 2. Line A plots the remaining weight percentage. Line B shows oxygen atomic percentage increasing with temperature, starting from 2 to 63 %. Line C illustrated the 90-16 carbon atomic percentage decrease according to temperature increment.

A notable oxygen increment and a relevant sample weight loss started at 350 °C. Hence, carbon diminish significantly in contrast to other elements.

Figure 3 shows thermal treated carbon nanotubes Raman spectra. The G band ( $E_{2G}$  Raman active modes) around 1575  $\text{cm}^{-1}$ , a typical band for graphite materials and for CNTs, was found in 270-400 °C oxidized samples; thus corroborating carbon nanotubes presence [13].

The D band, characteristic of disorder in graphitic lattice or defects in nanotubes [14], was observed close to 1340  $\text{cm}^{-1}$  in MWCNTs treated from 270 to 400 °C with different intensities. The spectra show another band at 2682  $\text{cm}^{-1}$  attributed to the overtone of D band, called G' [15].

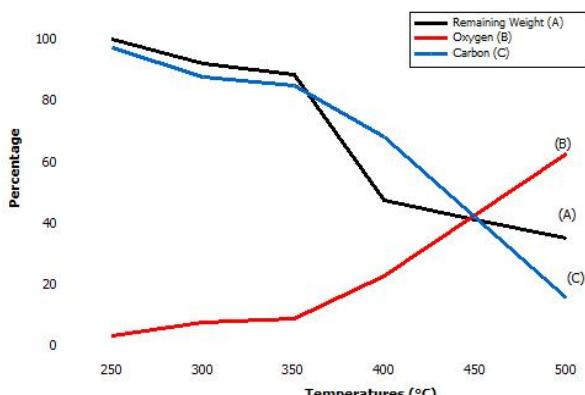


Figure 2. Samples elemental composition percentages relation to temperatures.

Table 1. Sample average atomic percentages treated at different temperatures

Elements	Temperatures (° C)				
	270	300	350	400	500
Oxygen	3.28	7.51	8.59	22.84	62.45
Carbon	89.783	87.42	84.91	68.07	15.32
Iron	06.94	05.07	06.50	9.09	22.23

Oxidized well aligned carbon nanotubes were confirmed by Raman spectra considering  $I_D/I_G < 1$  relation [16]. The highest relation for treated CNTs was 0.67 at 400 °C, suggesting major defects on this sample. Antunez *et al.* indicate that larger MWCNTs diameters showed a broaden D bandwidth measure by full width at half maximum (FWHM) [17]. The FWHM D bandwidth value decrease was observed through the treatment temperature increase; therefore it could be possible a MWCNTs diameter reduction.

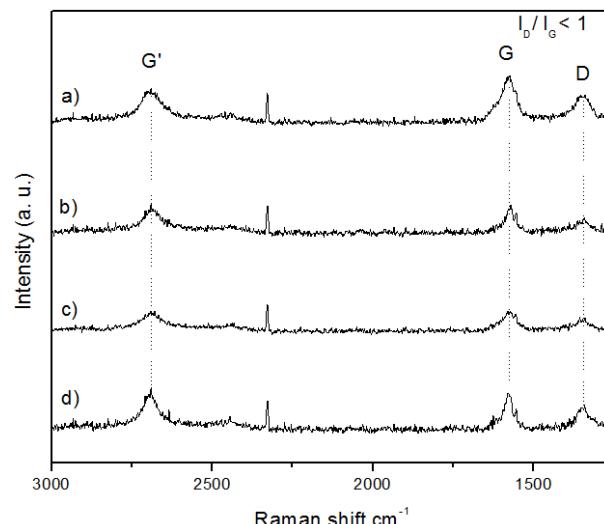


Figure 3. Raman Spectra for treated samples at: (a) 400 °C, (b) 350 °C, (c) 300 °C, (d) 270 °C

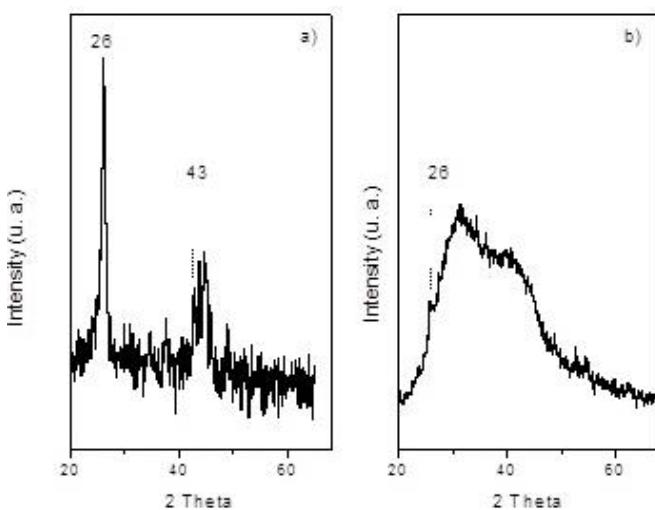


Figure 4. MWCNTs X-Ray Diffraction: (a) pristine, (b) treated at 270 °C.

For pristine MWCNTs a reflection peak centered at  $20 \approx 26^\circ$  in XRD spectrum, is shown in Figure 4(a), which is a characteristic hexagonal graphite (002) reflection [18, 19]. Also this peak is noticed in all CNTs samples after thermal treatment, but could be overshadowed, "Fig 4b", due to defects in the crystalline structure or secondary products formed subsequently. Hassan *et al.* reported a broaden (002) peak on CNTs after an acid treatment [20]. The (100) peak with  $20 \approx 43^\circ$  was reported by Cao *et. al* [21].

Pristine and oxidized carbon nanotubes FTIR spectra are shown in Figure 5 and Figure 6. The free OH stretch peak found in the MWCNTs at  $3616 \text{ cm}^{-1}$  widens and shifts to lower wave numbers, in thermal treated CNTs, indicating a hydrogen O-H bond. The  $\text{CH}_x$  vibrations were found on region around  $3060$  to  $2840 \text{ cm}^{-1}$ . The peak at  $3060 \text{ cm}^{-1}$  is associated to the stretch for  $\text{sp}^2\text{-CH}$  in aromatic rings [22]. The oxidation of CNTs heated above  $270^\circ \text{ C}$  could be proved by the disappearance of these signals. Intensities around  $2917 \text{ cm}^{-1}$  can be attributed to stretching vibration of  $\text{CH}_2$  and  $\text{CH}_3$ ; hydrogen interactions are common in carbon nanotubes obtained by CVD [23].

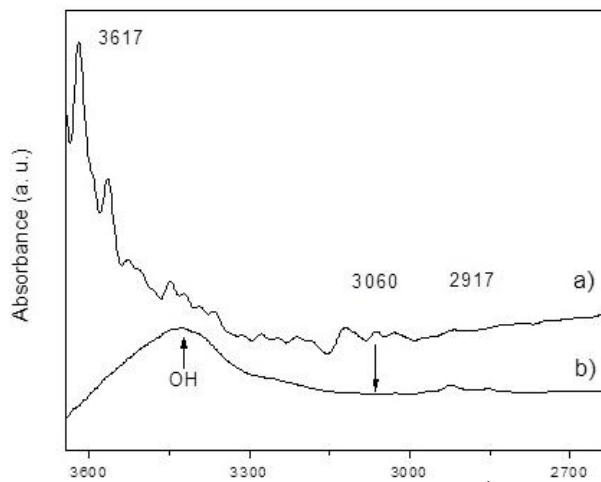


Figure 5. MWCNTs FTIR spectra from  $3650$  to  $2650 \text{ cm}^{-1}$ : (a) pristine, (b) treated at  $270^\circ \text{ C}$

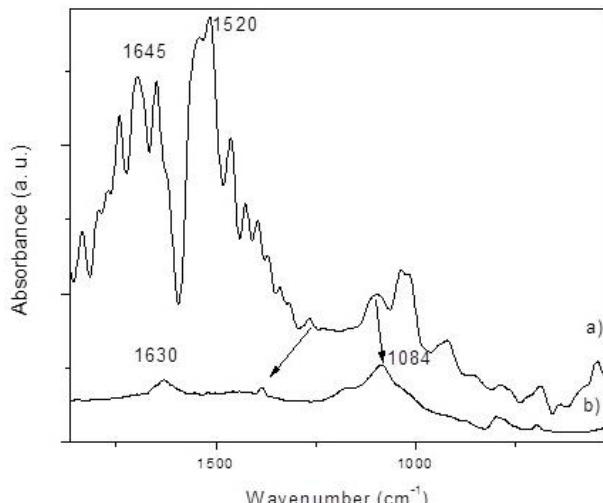


Figure 6. MWCNTs FTIR spectra from  $1800$  to  $500 \text{ cm}^{-1}$ : (a) pristine, (b) treated at  $270^\circ \text{ C}$

Lost in  $\text{CH}_x$  species were reported by Douglas *et al.* after carbon exposure to ozone with  $300 \text{ K}$  temperature; leading to the production of  $-\text{COOH}$  species [24]. Bands at  $1670$ – $1600 \text{ cm}^{-1}$  are related to the  $\text{C=O}$  conjugation with two aromatic rings. The stretching skeleton vibrations for most carbon materials, can be found in the  $1582$ – $1400 \text{ cm}^{-1}$  range for pristine carbon nanotubes [23]. The  $1630 \text{ cm}^{-1}$  band for treated CNTs could be attributed to the conjugation of  $\text{C=C}$  with a carbonyl group, showing lower intensities. The  $1084 \text{ cm}^{-1}$  signal behavior might be explained by the shift of  $\text{C-O}$  absorptions to lower frequencies when the OH is attached to a ring [22].

#### 4. Conclusion

This research proposes a methodology to functionalize carbon nanotubes avoiding traditional multi-step processes; thus leading to a simpler, faster and one step process. According to the temperature increments, there is a notable oxygen increase, however carbon content diminishes in samples; this is demonstrated by EDS and FTIR spectra. SEM micrographs did not show carbon nanotubes in samples treated above  $500^\circ \text{ C}$ . Results showed that carbonyl and hydroxyl functionalized groups could be obtained at  $270$ – $350^\circ \text{ C}$  with minimum weight loss. The results shown by the proposed functionalization methodology could lead to a cheap and environmental friendly process to be further applied.

#### 5. Acknowledgment

Acknowledgments to "Universidad Michoacana de San Nicolas de Hidalgo" Scientific Research Coordination projects and to "PRODEP Nanostructured Materials" Collaboration Network (SEP, Mexico).

#### References

- [1]. N. Sahoo, S. Rana, J. Whan, L. Li, S. Chana, *Prog. Polym. Sci.* **37**, 837 (2003).
- [2]. M. Terrones, A.R. Botello-Méndez, J. Campos-Delgado, F. López-Urías, Y.I. Vega-Cantú, F.J. Rodríguez-Macías, A.L. Elfas, E. Muñoz-Sandoval, A.G. Cano-Márquez, J.C. Charlier, H. Terrones, *Nano Today* **5**, 351 (2010).
- [3]. J. Thomassina, I. Huynen, R. Jerome, C. Detrembleur, *Polymer* **51**, 115 (2010).
- [4]. L. Stobinski, B. Lesiaka, L. Kövér, J. Tóth, S. Biniak, G. Trykowski, J. Judek, *J. of alloys and compounds* **501**, 77 (2010).
- [5]. B. Scheibe, E. Borowiak-Palen, R. Kalenczuk, *Mater. Charact.* **61**, 185 (2010).
- [6]. B. Kim, W. Sigmund, *Langmuir* **20**, 8239 (2010).
- [7]. F. López-Urías, M. Terrones, H. Terrones, *Carbon* **84**, 317 (2015).
- [8]. L. Ravelo-Pérez, A. Herrera-Herrera, J. Hernández-Borges, M. Rodríguez-Delgado, *J. Chromatogr. A* **1217**, 2618 (2010).
- [9]. C. Li, D. Wang, T. Liang, X. Wang, J. Wu, X. Hu, J. Liang, *Powder technology*, **142**, 175 (2004).
- [10]. N. Dementev, S. Osswald, Y. Gogotsi, E. Borgue, *J. Mater. Chem.* **19**, 7904 (2009).
- [11]. A. Gómez, P. González, L. García, F. Granados, N. Flores, V. López, L. Domratczeva, *J. Anal. Appl. Pyrol.* **113**, 483 (2015).

[12]. L. Domratcheva, E. Domracheva, A. Zaitsev, L. Mikhalitsyn, G. Markin, A. Ob'edkov, L. Leites, B. Kaverin, S. Bukalov, G. Domrachev, Fullerenes, Nanotubes and Carbon Nonstructures 14, 193 (2006).

[13]. Y. Shiratori, H. Hiraoka, M. Yamamoto, Mater. Chem. Phys. **87**, 31 (2004).

[14]. S. Lefrant, I. Baltog, M. Baibarag, J. Schreiber, O. Chauvet, Phys. Rev. B **65**, 235 (2002).

[15]. M. Dresselhaus, G. Dresselhaus, R. Saitoc , A. Joriod, Phys. Rep. **409**, 47 (2005).

[16]. Y. Jung, D. Jeon, Appl. Surf. Sci., **193**, 129 (2002).

[17]. E. Antunes, A. Lobo, E. Corat, B. Trava-Airoldi, Carbon **45**, 913 (2007).

[18]. G. Allaedini, P. Aminayi, S. Tasirin, J. Nanomater. **501**, 961231 (2015).

[19]. P. Mahanandia, P.N. Vishwakarma, K.K. Nanda, V. Prasad, K. Barai, A.K. Mondal, S. Sarangi, G.K. Dey, S.V. Subramanyam, Solid State Commun. **145**, 143 (2008).

[20]. H. Khani, O. Moradi, J. Nanostr. Chem. **3**, 73(2013).

[21]. A Cao, C Xu, J Liang, D Wu, B Wei, Chem Phys. Lett. **344**, 13 (2001).

[22]. D. Pavia, G. Lampman, G. Kriz, J. Vyvyan, Introduction to spectroscopy, 4th Ed. (Brooks Cole, 2008).

[23]. L.Teng, T. Tang, J. Zhejiang Univ-Sc A **9**, 720 (2008).

[24]. D. Mawhinney, J. Yates, Carbon **39**, 1167 (2001).